

AD-A085 121

DEFENCE RESEARCH INFORMATION CENTRE ORPINGTON (ENGLAND)

F/6 1/5

THE FRICTION CLASSIFICATION OF RUNWAYS (U)


DEC 79 R W SUGG, I BEATY, R J NICHOLLS

UNCLASSIFIED


DRIC-BR-70258

NL

1-1
2-1
3-1

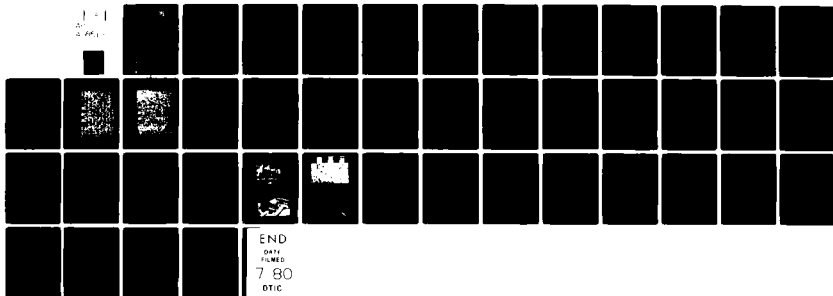

END
DATA
FILMED
7 80
DTIC

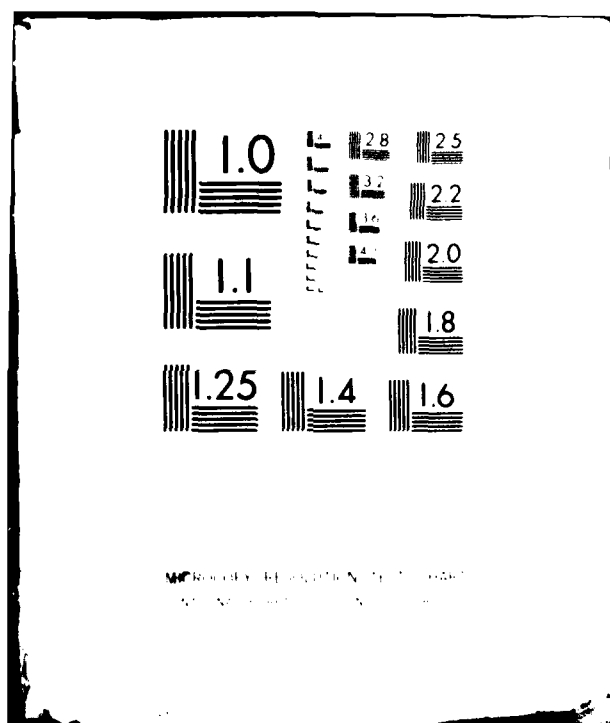

UNLIMITED

BR70258

S&T-MEMO-6-79



LEVEL

①

PROCUREMENT EXECUTIVE MINISTRY OF DEFENCE

**THE FRICTION CLASSIFICATION
OF RUNWAYS**

DDC
RECEIVED
FEB 7 1980
E

R W SUGG, I BEATY AND R J NICHOLLS

ISSUED BY:
**DEFENCE
RESEARCH
INFORMATION
CENTRE**

Station Square House, St. Mary Cray, Orpington, Kent, BR5 3RE

UNLIMITED

80

1 28

12

S&T-MEMO-6-79

ADA 085121

DDC FREE COPY

UNLIMITED

14 DRIC-BR-70258
S/T-MEMO-6-79

6 THE FRICTION CLASSIFICATION OF RUNWAYS,

10 R. W. SUGG
~~Memorandum~~ Engineering Research and Development 1, St Giles Court, London
I. BEATY R. J. NICHOLLS
Cranfield Institute of Technology

SUMMARY

The fundamental principles regarding the design of runway surfaces to provide high friction under wet conditions are well known and have been put into practice for some time. In the past a locked wheel trailer has been used to assess the relative friction of runways by making measurements at a number of isolated points on the surface. With the development of the Continuous Recording Runway Friction Meter (Mu-Meter) and a runway self wetting system contained in the tow vehicle, it has been possible to obtain a permanent record showing the friction reading along the entire length of a runway. This S&T Memo describes the method developed to carry out such a trial together with its associated Standard Friction Classification Table.

Use of the Mu-Meter under natural rain conditions has demonstrated that aircraft aquaplaning could sometimes occur in local areas. A method is described how these areas can be identified and how it is combined with the self wetting trial to give a proper friction evaluation of a runway.

The relationship in Mu-Meter readings when using the US Federal Aviation Administration and UK Ministry of Defence methods of runway friction classification, have been determined.

Copyright © Controller HMSO London 1979

DEFENCE RESEARCH INFORMATION CENTRE
Station Square House
St Mary Cray
Orpington
Kent BR5 3RE

11
Issue date: December 1979

12 44

(1)

UNLIMITED

407040

CONTENTS

1. Introduction
2. Self Wetting Trials
3. Natural Rain Trials
4. Trials Report
5. Discussion
6. Conclusions
7. References

TABLES

1. Critical Water Depths which will initiate aquaplaning.
2. Runway Classification Table - NATO Stanag 3811.
3. Extract from NATO Stanag 3634 - Braking Action Table.

FIGURES

1. Grooved Asphalt.
2. Porous Friction Course.
3. Relationship between Mu-Meter reading and aircraft stop distance from recent trials.
4. A comparison between Mu-Meter traces under natural rain and self wetting conditions on a military runway surfaced with $\frac{1}{8}$ " pre-coated grit.
5. A comparison between Mu-Meter traces under natural rain and self wetting condition on an asphalt runway.
6. A comparison between Mu-Meter traces under natural rain and self wetting conditions on a civil runway surfaced with $\frac{1}{8}$ " pre-coated grit.
7. A comparison between Mu-Meter traces under natural rain and self wetting conditions on a civil Marshall asphalt runway.
8. Relationship between Mu-Meter readings at different speeds under self wetting conditions.
9. Relationship between Mu-Meter readings using U.S Federal Aviation Administration and U.K Ministry of Defence self wetting methods.
10. Results of Mu-Meter Friction Classification of some runways using the NATO Stanag 3811 method.

Accession For	
NTIS	GRII
DDC TAB	Unannounced
Justification	
By	
Distribution	
Availability	
Dist	Available for special
A	

FIGURES (Contd)

11. Mu-Meter tracks for Runway Classification trials under natural rain conditions.
12. Mu-Meter Wet Test Log.
13. Friction contours on a civil runway.

APPENDIX

- A. An example of a Runway Friction Classification Trial Report.

23

1. Introduction

1.1 One of the operational problems that was created when aircraft landing speeds started to increase was the ability to stop within the confines of the runway, particularly when wet. The most immediate outcome was the introduction of runway grooving (Fig 1) and later the development of the Porous Friction Course (Fig 2). The grooves which were $\frac{1}{2}$ " wide, $\frac{1}{8}$ " deep of 1" centres, improved the macrotexture of the surface and as explained in Ref 1, increased the friction level at high speeds. The Porous Friction Course consists of a layer of aggregate between 1" and 2" thick which is so graded when it is laid there are interconnecting drainage holes. These holes first allow the water to drain in a vertical direction until it meets the impervious surface on which the PFC is laid, then sideways down the crossfall. Provided the runway is correctly profiled no water collects on the surface.

1.2 A high speed trailer developed by the Transport and Road Research Laboratory was used to measure runway friction. This trailer could be towed at speeds up to 100 mph and measured friction by locking the test wheel for a short distance and it was established the results did bear some relation to pilots opinion. The test method was to select several small areas on the runway which were wetted by a water bowser. Runs were then made at speeds between 20 and 100 mph and runways compared by the friction value at 80 mph. Additional water was applied when the surface condition was considered to have changed sufficiently to affect friction.

1.3 Since the test areas were relatively small and the water depth a matter of opinion, the equipment was limited in its accuracy and the extent of its survey. With the development of a Continuous Measuring Runway Friction Meter (Mu-Meter) (Ref 2) for use in the Royal Air Force,

the situation changed considerably since a self-wetting system was also developed which could be carried in the towing vehicle to deposit a standard quantity of water ahead of each test wheel as well as provide a continuous record of friction from end-to-end of the runway. It was now possible to create a more scientific method by which runway friction could be judged. The result of trials using several different types of aircraft under differing runway conditions demonstrated that a relationship could be established between aircraft stop distance and average Mu-Meter reading. See Fig 3 and Ref 3 Fig 9. Consequently the Mu-Meter could be used with confidence to compare runway friction.

1.4 The initial Service requirement for the Mu-Meter was to provide a daily indication of the runway state under natural rain conditions. When these recordings became available it was found that the variations in friction along the runway could be very different from those in its self-wetting mode. see Figs 4, 5, 6 and 7. It was found that these variations were due, almost entirely, to changes in water depth caused by the slight unevenness of the runways.

1.5 Tests with aircraft at the Cranfield Institute of Technology (Ref 4) established the following table which gives the depth of water needed to cause acuaplaning on different types of runway surface.

Table 1 - Critical Water Depths which will Initiate Acuaplaning

Surface	Percentage Velocity is above Acuaplaning Speed	
	10%	40%
Brushed Concrete	.06	.04
Scored Concrete	.12	.06
$\frac{1}{8}$ " Grooved Concrete	-	.12
$\frac{1}{8}$ " Grooved Asphalt	-	.15
Marshal Asphalt	-	.04
$\frac{1}{4}$ " Grooved Concrete	.23	.15

1.6 Tests in the "critical water depths" of Table 1 gave Mu-Meter readings of between .3 and .4. Some Mu-meter recordings of runways under natural rain conditions gave readings, in some areas, below this figure (see Figs 4, 5, 6 and 7). Although the length of these potential aquaplaning areas was often short, a succession of such areas could cause the aircraft wheels to spin down resulting in a dangerous condition where a type of aquaplaning could continue down to a very low speed. It was clear that an important part of a test to determine the classification of a runway would have to be a check if such conditions existed.

1.7 The classification had therefore to consist of 2 separate and distinct parts. Firstly the general friction level measured at a standard speed under standard wetness conditions where it can be compared with other known surfaces and be related to a table giving recommended actions. Secondly, tests under natural rain conditions over the full length and width of runway where the presence and location of low friction areas caused by ponding can be established.

2. Self-Wetting Trials

2.1 The self-wetting system used by the Ministry of Defence consists of a 70 Imperial gallon rigid tank fitted behind the driving seat of a 3 litre Ford Capri and a 12 volt motor driven pump which can be regulated to deliver up to a maximum of 50 gallons of water per minute. The water is discharged just ahead of each test wheel through brushes in contact with the runway. The brushes reduce the dispersion of the water when the equipment is used at high speed. See Appendix A Plates A1 and A2. In addition to the trace recorder in the Mu-Meter itself, the vehicle contains a repeater in the instrument panel so that the readings can be seen in the driving position during test runs.

2.2 After carrying out the standard calibration checks called for in Ref 2, runs are made down the runway at speeds of 20, 40, 60 and 80 mph

along a track approximately 5 metres from the centre-line, discharging water ahead of the test wheels at the rate of 10, 20, 30 and 40 Imperial gallons per minute respectively. The object of changing the water discharge rate with speed is to maintain a standard water depth under the test wheels, this depth has been calculated as approximately .015".

2.3 The shape of the speed/friction curve obtained by plotting the test data from these runs, shows how much friction drops with speed and is a factor that must be taken into account in the final report. The runway itself is classified in accordance with the following table using the average reading at 80 mph obtained from the Mu-Meter recorder trace.

Table 2 - Runway Classification Table - NATO Stanag 3811

Average Mu-Meter Reading at 80 mph	Classification Standard	Action
.6 and above	Acceptable	None
.59 to .4	Marginal	Inspect and rectify as necessary
.39 and below	Unacceptable	Corrective action required

2.4 There will be occasions when the average of the end-to-end friction value will be in the "acceptable" category, but certain areas may give low readings due to rubber deposits or other reasons. Where these readings fall below .39 in the braking area, rectification action should be taken if the contaminated area is long enough to affect stop distance in such a way as to constitute a hazard.

2.5 The use of a high speed for this type of work is favoured since it gives a clearer indication of the relative merits of different surfaces particularly when they are at approximately the same friction level. However, tests have shown that provided a correction is made it is possible though less accurate, to use the same Classification Standard in Table 2 by running the Mu-Meter at a lower speed. See Fig. 8. The relationship between the

Mu-Meter readings using the US Federal Aviation Administration and UK Ministry of Defence test speeds and self wetting discharge rates is at Fig. 9.

2.6 A typical report of a high speed friction trial is at Part 1 of Appendix A. This shows the standard pro forma used for the results, how friction is plotted against speed and the type of photographs taken to describe the test surface. To serve as a comparison for test results, Fig 10 is a list of some runways that have been tested and placed in their friction order together with the NATO Stanag 3011 Classification Standard.

3. Natural Rain Trials

3.1 As explained in paras 1.6 and 1.7 this part of the runway friction classification trial is to determine if there are areas where a potential aircraft aquaplaning risk exists. Where these areas are present, they are frequently caused by undulations in the runway, allowing water to collect. For this trial a Mu-Meter has to be positioned at the airfield ready for it to rain. Because vehicles used on airfields cannot be expected to have the performance to pull a Mu-Meter at 20 mph, a speed of 40 mph has been used as the standard for this part of the classification trial. To make a survey of the whole runway width, the test tracks are specified together with their sequence. See Fig 11.

3.2 Using the event bulb in the vehicle cab each run is identified as follows:

- 2 squeezes at the start threshold
- 1 squeeze as soon as 40 mph is reached
- 1 squeeze just before decelerating
- 2 squeezes at the finish threshold.

The Remote Read-out Unit (if fitted) is operated in the normal manner ie switched on when 40 mph is reached, changing channels at each third of the runway and switching off before decelerating. In addition the following are observed.

3.2.1 At regular intervals the trace is to be marked with the run number. At this point check to ensure sufficient recording roll remains to continue the operation and that the Mu-Meter is functioning correctly.

3.2.2 The test wheels are splayed out at all times, even if the vehicle is temporarily cleared from the runway.

3.2.3 The Wet Test Log at Fig 12 is used to keep a record of all runs.

3.2.4 At the end of the runs a copy of the rainfall trace for the day (if available) is attached to the Wet Test Log.

3.2.5 To confirm the calibration of the Mu-Meter, a run is made in dry conditions as soon as possible after the wet runs at a position 2 metres to one side of the centre-line. The result should be recorded in the Wet Test Log.

3.3 Since the traces have all been marked to show the beginning and end of the runway, an inspection of the trace can show where areas of low friction occur on the actual runway along each track. By associating the readings of one track with another it is possible to show how areas of low friction occur across the runway as well as along its length. See Fig 13.

3.4 The following friction table from Stanag 3634 is used to judge the runway condition.

Table 3 - Extract from NATO Stanag 3634 - Braking Action Table

Mu-Meter Reading at 40 mph	Verbal Description
.5 and above	Good
.49 to .35	Medium
.34 and below	Poor

3.5 As shown in para 1.6 a potential aquaplaning condition can exist when the Mu-Meter reading is below .4 and this figure is now used when indicating when and where the runway surface is below standard. See Fig 13.

4. Trials Report

4.1 Appendix A is an example of a final test report where the results of both the self-wetting and natural rain trials form Parts 1 and 2 of a combined document. Part 1 contains a standard test proforma for use at the classification speed of 80 mph whilst at Table 1A is a record of Mu-Meter readings at speeds of 20, 40, 60 and 80 mph which are plotted at Fig 7A and in this case shows a small drop off at high speed. Figs 2A to 6A are typical Mu-Meter traces along different tracks and show an inherently high friction reading.

4.2 Part 2 of Appendix A describes the test under natural rain conditions with a typical trace marked with the danger areas. Fig 2B has been constructed using the method described in paras 3.3 and 3.5 to show the areas with a potential aquaplaning risk. Another example of a combined report is at Appendix C of Ref 3.

5. Discussion

5.1 As the result of trials with a number of aircraft it has been demonstrated that a relationship can be established between Mu-Meter reading and aircraft stop distances under wet conditions. This fact gives confidence that the equipment can be used to conduct a runway friction survey which is meaningful to aircraft performance. A set of standard conditions and a Friction Table have therefore been developed so that the measured friction can be compared with other known runways and a decision made if and what remedial action to take.

5.2 It has been demonstrated that whilst self-watering trials will measure the inherent friction they do not always represent the friction under natural rain conditions. This is partly due to variations in water depth along the runway which may get worse with time.

5.3 Since aircraft trials have demonstrated that it only requires a water depth of .04 inches on some surfaces to cause aquaplaning, it can be seen

that only a small change in runway slope is required to create a low friction area. It is therefore not surprising that results from runways under natural rain conditions have introduced an additional and vital condition which must be considered in the friction classification of runways.

5.4 Fortunately tests already conducted with the Mu-Meter in water depths which had been shown to cause aircraft aquaplaning, demonstrated that a dangerous condition could exist below a reading of 0.4. This figure is now used in runway classification work to indicate the areas where potential aquaplaning conditions exist.

6. Conclusion

6.1 Equipment used for this type of work must have been demonstrated as giving friction readings which can be related to the stop distances of different types of aircraft. It must also have been tested to determine the readings at which it will indicate potential aquaplaning conditions exist.

6.2 The friction classification of runways under wet conditions must consist of two parts. First, a survey from end to end using a self-wetting system to measure inherent friction. Second, a series of runs along defined tracks under natural rain to provide the data to determine the extent and position of possible aquaplaning areas.

6.3 This S & T Memo describes a satisfactory method now being used to conduct a runway friction classification using the Mu-Meter.


7. References

(1) R W Sugg - An Investigation into Measuring Runway Surface Texture by the Grease Patch and Outflow Meter Methods. Ministry of Defence S&T Memo 2/79.

(2) Continuous Recording Runway Friction Meter - Ministry of Defence Air Publication AP 11QJ-1001-126A.


(3) I Beaty and R W Sugg - Trials to compare the stopped performance of three anti-skid systems and to demonstrate methods of determining aircraft stop distances on the Standard Military Reference Wet Surface, Ministry of Defence S&T Memo 3/79. AC78533

(4) J R Williams - The Effects of Runway Surface Texture on Aquaplaning - Ministry of Defence S&T Memo 11/71.

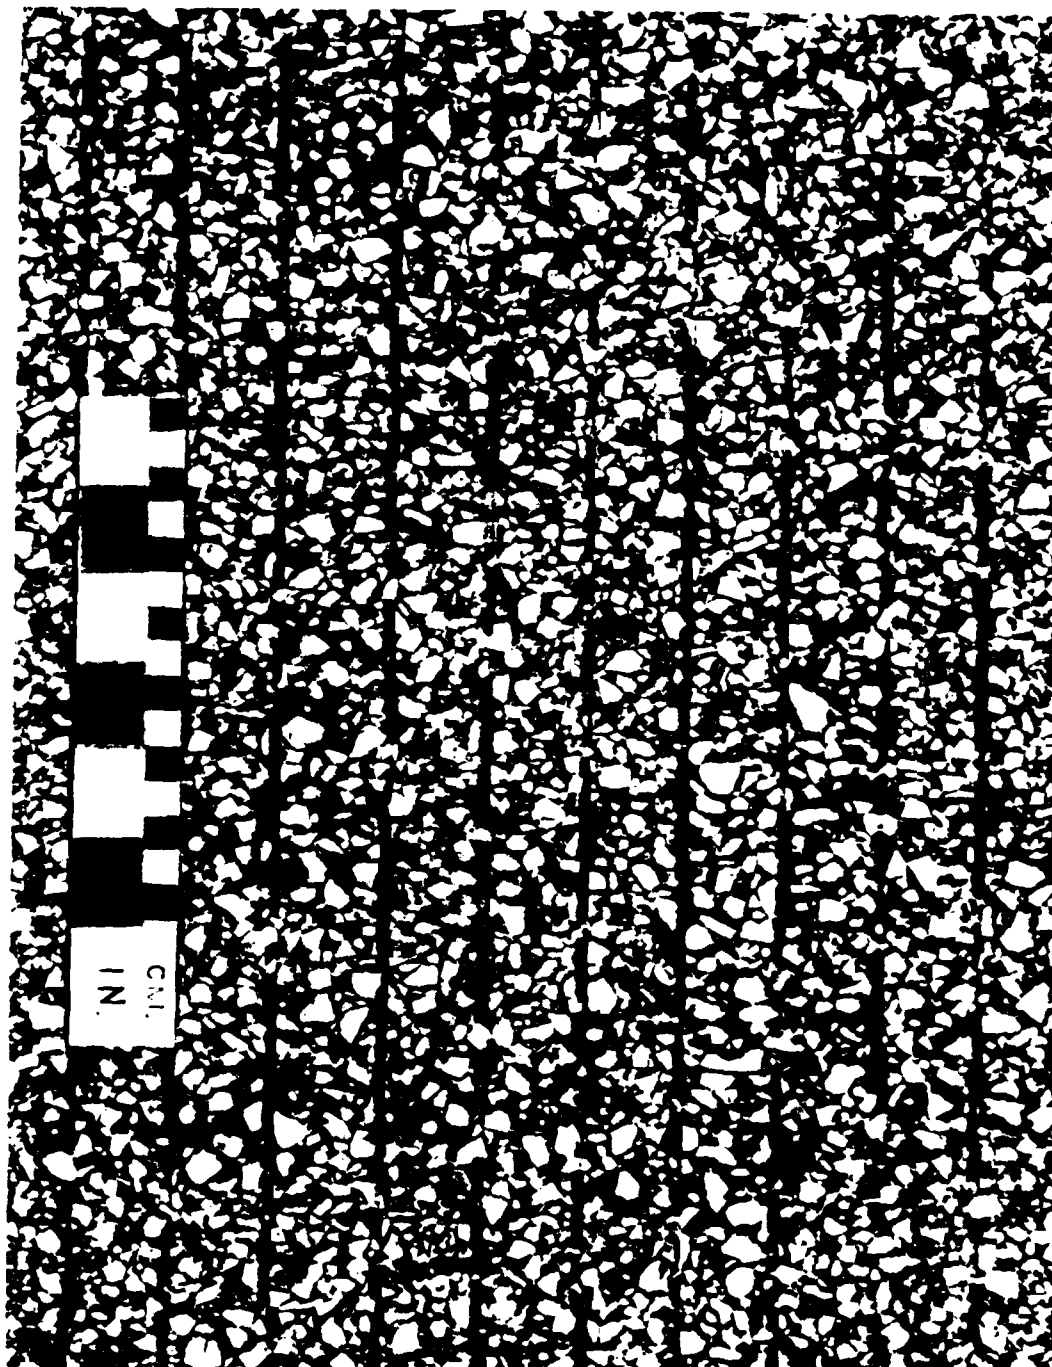


1/8" x 1/8" x 1" GROOVED ASPHALT

FIG. 1

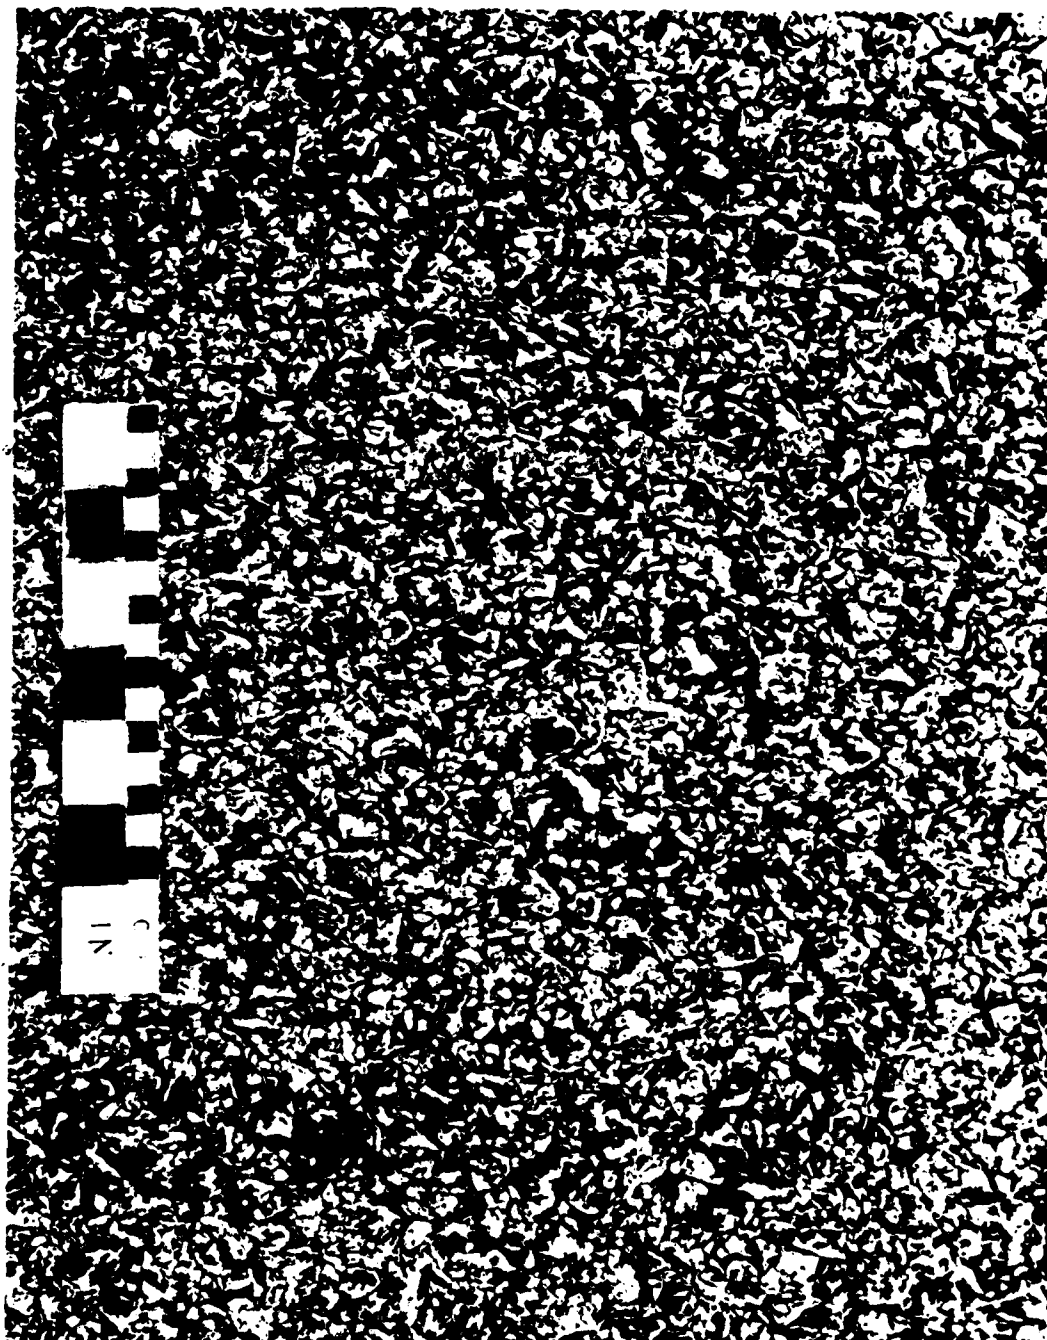



POROUS FRICTION COURSE

FIG. 2

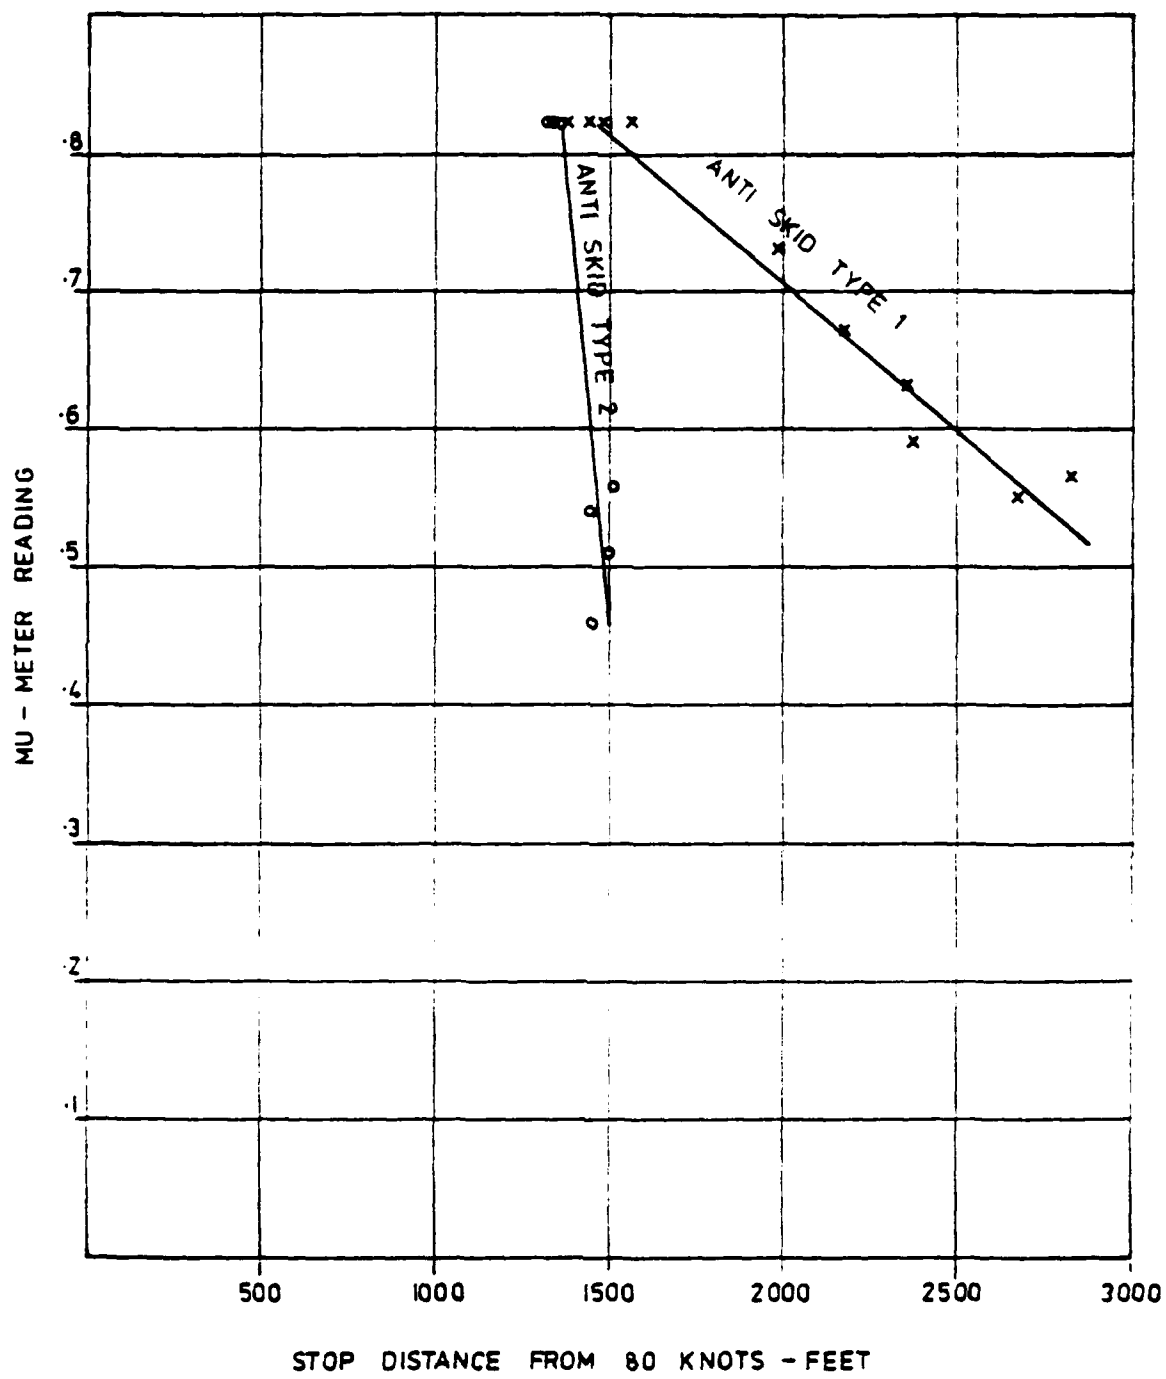


RELATIONSHIP BETWEEN MU-METER READINGS AND AIRCRAFT
STOP DISTANCES FROM RECENT TRIALS

FIG. 3

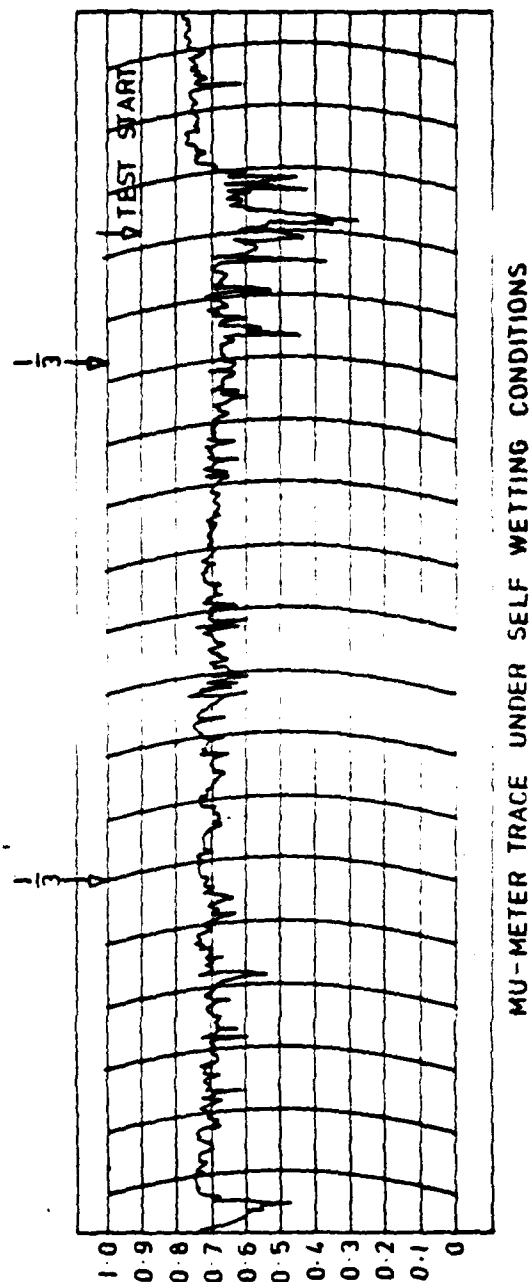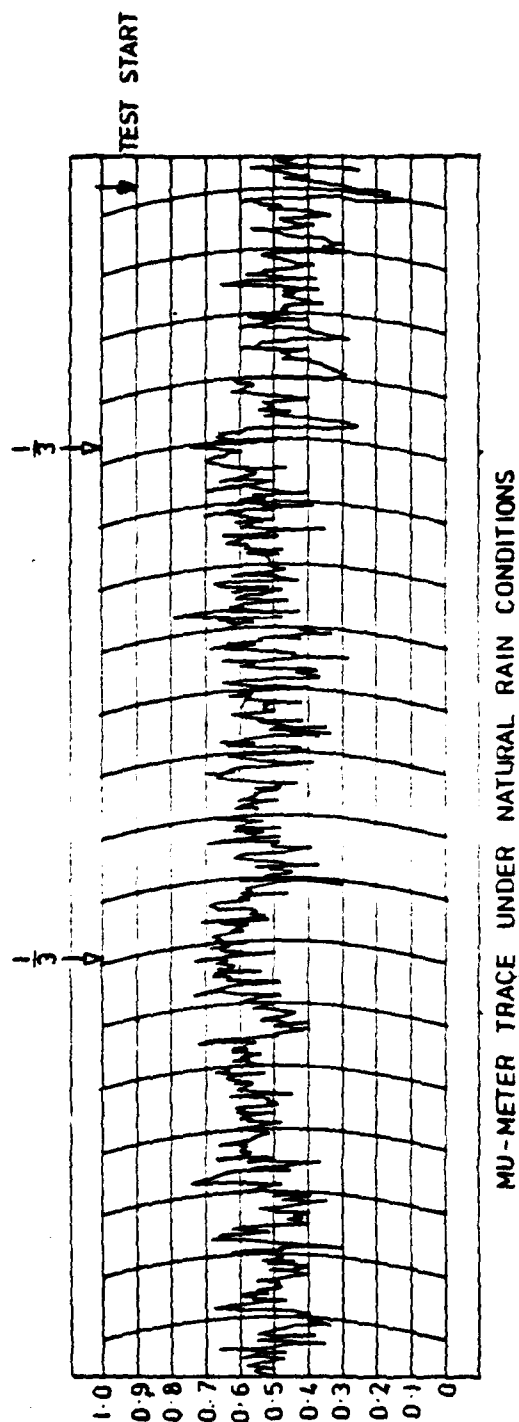


A COMPARISON BETWEEN MU-METER TRACES UNDER NATURAL RAIN AND SELF WETTING CONDITIONS ON A MILITARY RUNWAY SURFACED WITH $\frac{1}{8}$ PRE COATED GRIT

FIG. 4

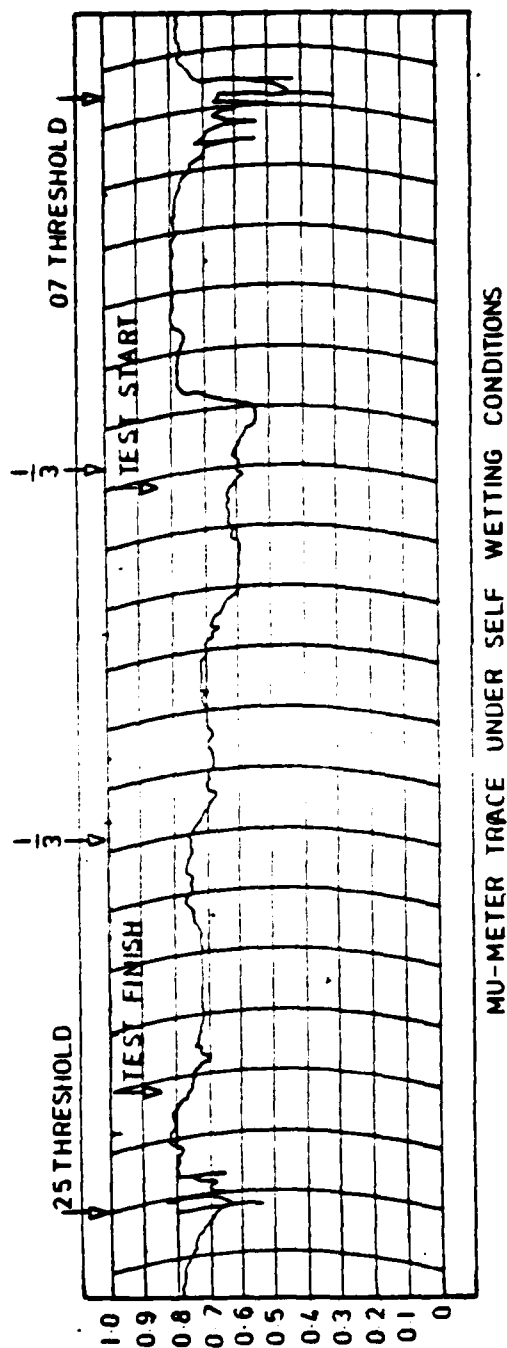

MU-METER TRACE UNDER SELF WETTING CONDITIONS

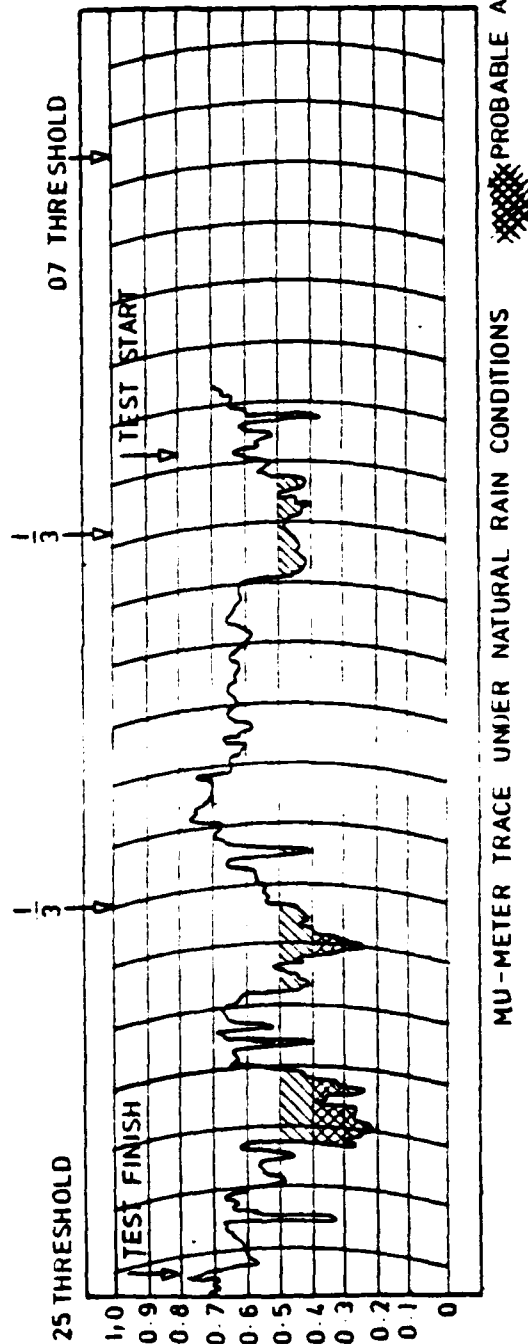


MU-METER TRACE UNDER NATURAL RAIN CONDITIONS


PROBABLE AQUAPLANING AREAS

A COMPARISON BETWEEN MU-METER TRACES UNDER NATURAL RAIN AND SELF WETTING CONDITIONS ON AN ASPHALT MILITARY RUNWAY

FIG. 5

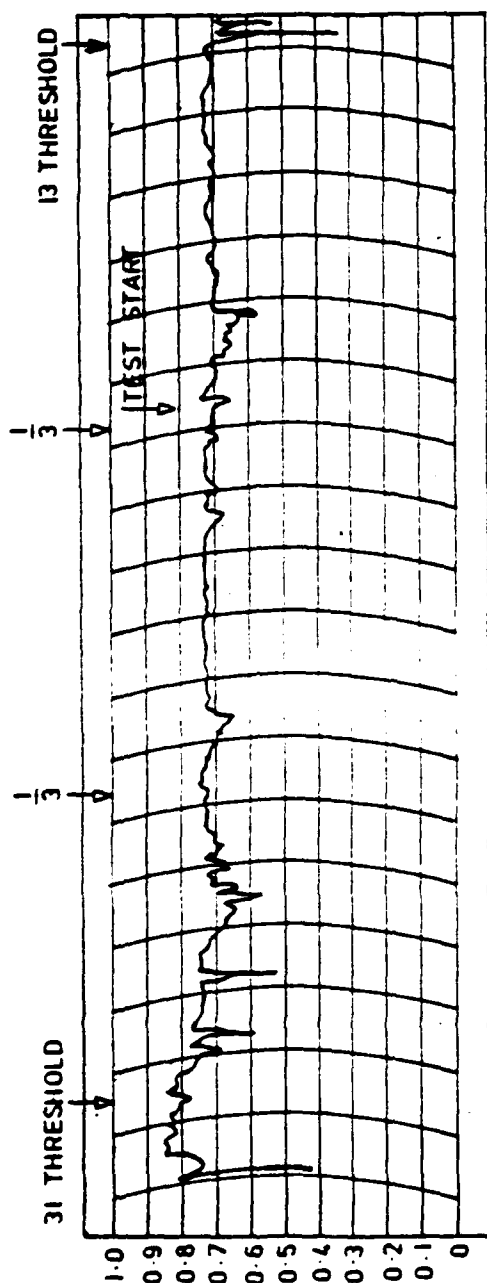


MU-METER TRACE UNDER SELF WETTING CONDITIONS

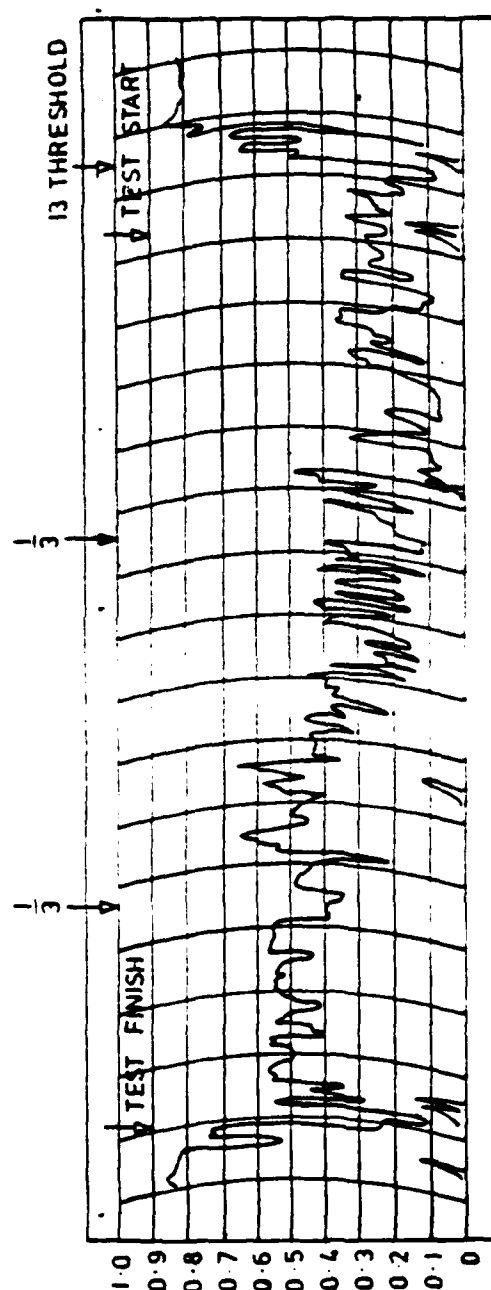


MU-METER TRACE UNDER NATURAL RAIN CONDITIONS

A COMPARISON BETWEEN MU-METER TRACES UNDER NATURAL RAIN AND SELF WETTING CONDITIONS ON A CIVIL RUNWAY SURFACED WITH $\frac{1}{8}$ PRE COATED GRIT

FIG. 6

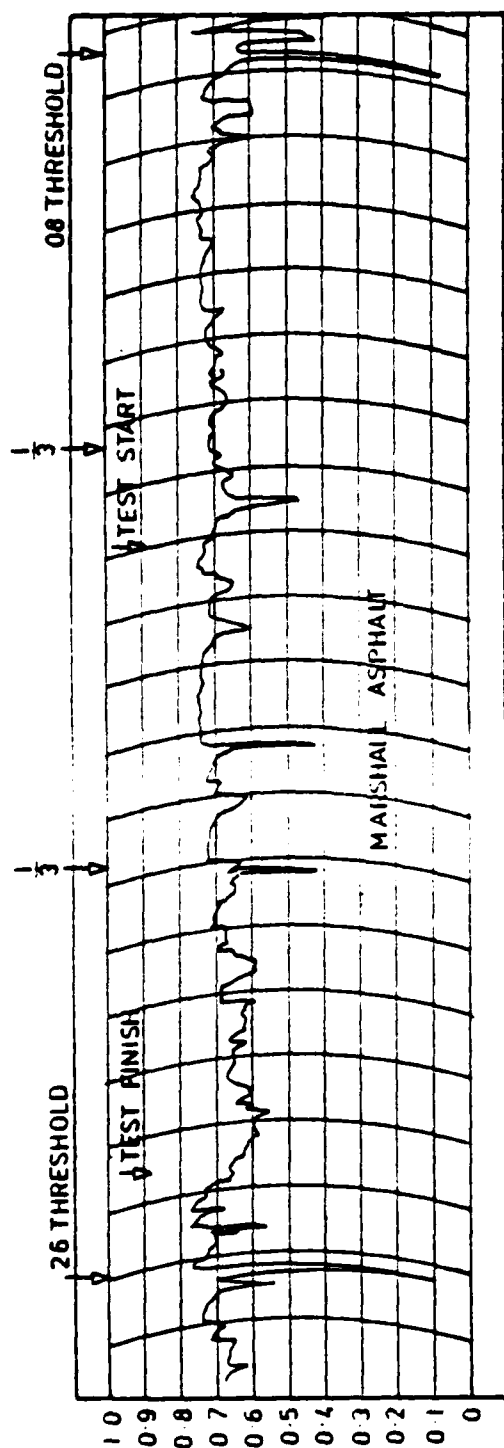


MU-METER TRACE UNDER SELF WETTING CONDITIONS

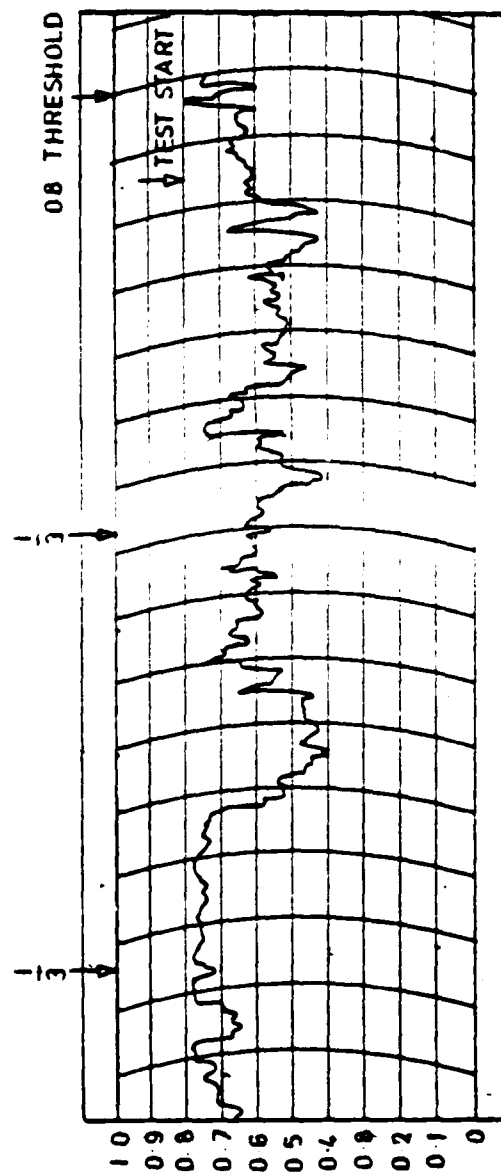

MU-METER TRACE UNDER NATURAL RAIN CONDITIONS

A COMPARISON BETWEEN MU-METER TRACES UNDER NATURAL RAIN AND SELF WETTING CONDITIONS ON A CIVIL MARSHALL ASPHALT RUNWAY

FIG. 7

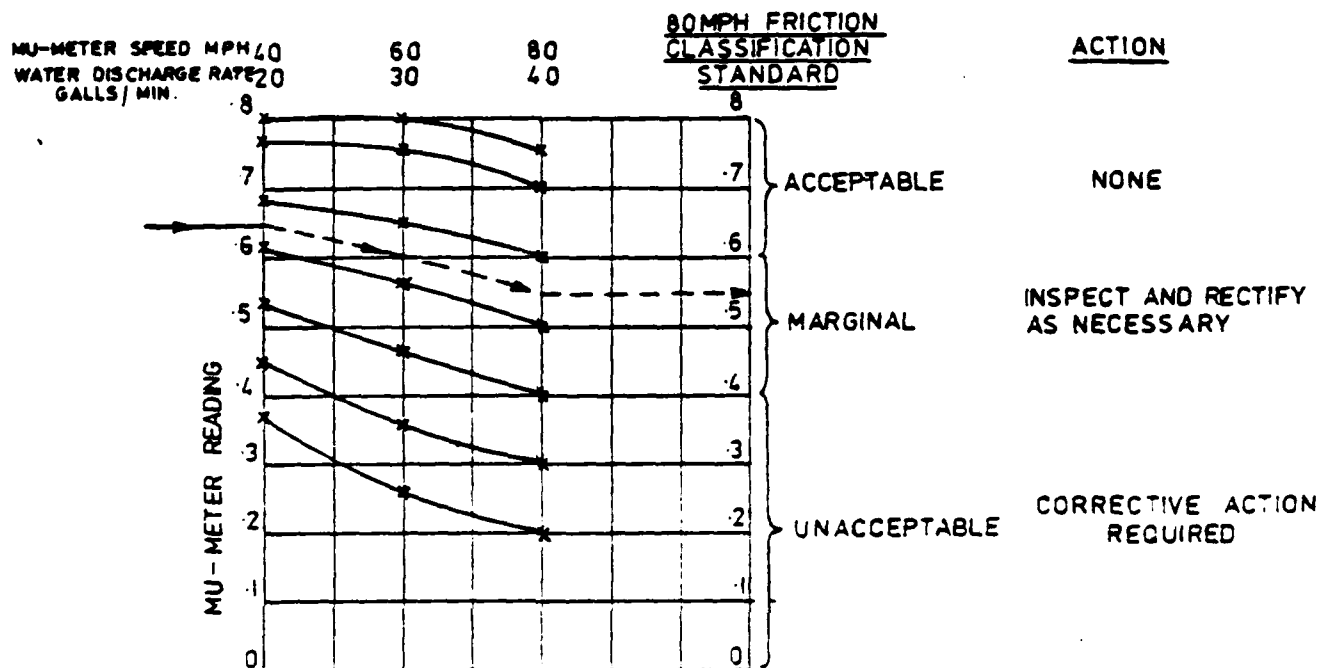


NOTE 1 THE SPEED RELATIONSHIP IS TAKEN FROM S & T MEMO 2/79

NOTE 2 THE CLASSIFICATION STANDARD AND ACTION IS FROM STANAG 3811

RELATIONSHIP BETWEEN MU-METER READINGS AT DIFFERENT SPEEDS UNDER SELF WETTING CONDITIONS

EXAMPLE -A READING OF 6.5 AT 40 MPH USING A WATER DISCHARGE RATE OF 20 GAL/MIN IS THE EQUIVALENT OF 5.5 AT 80 MPH USING A DISCHARGE RATE OF 40/GALL MIN AND GIVES A FRICTION CLASSIFICATION STANDARD OF 'MARGINAL'


FIG. 8

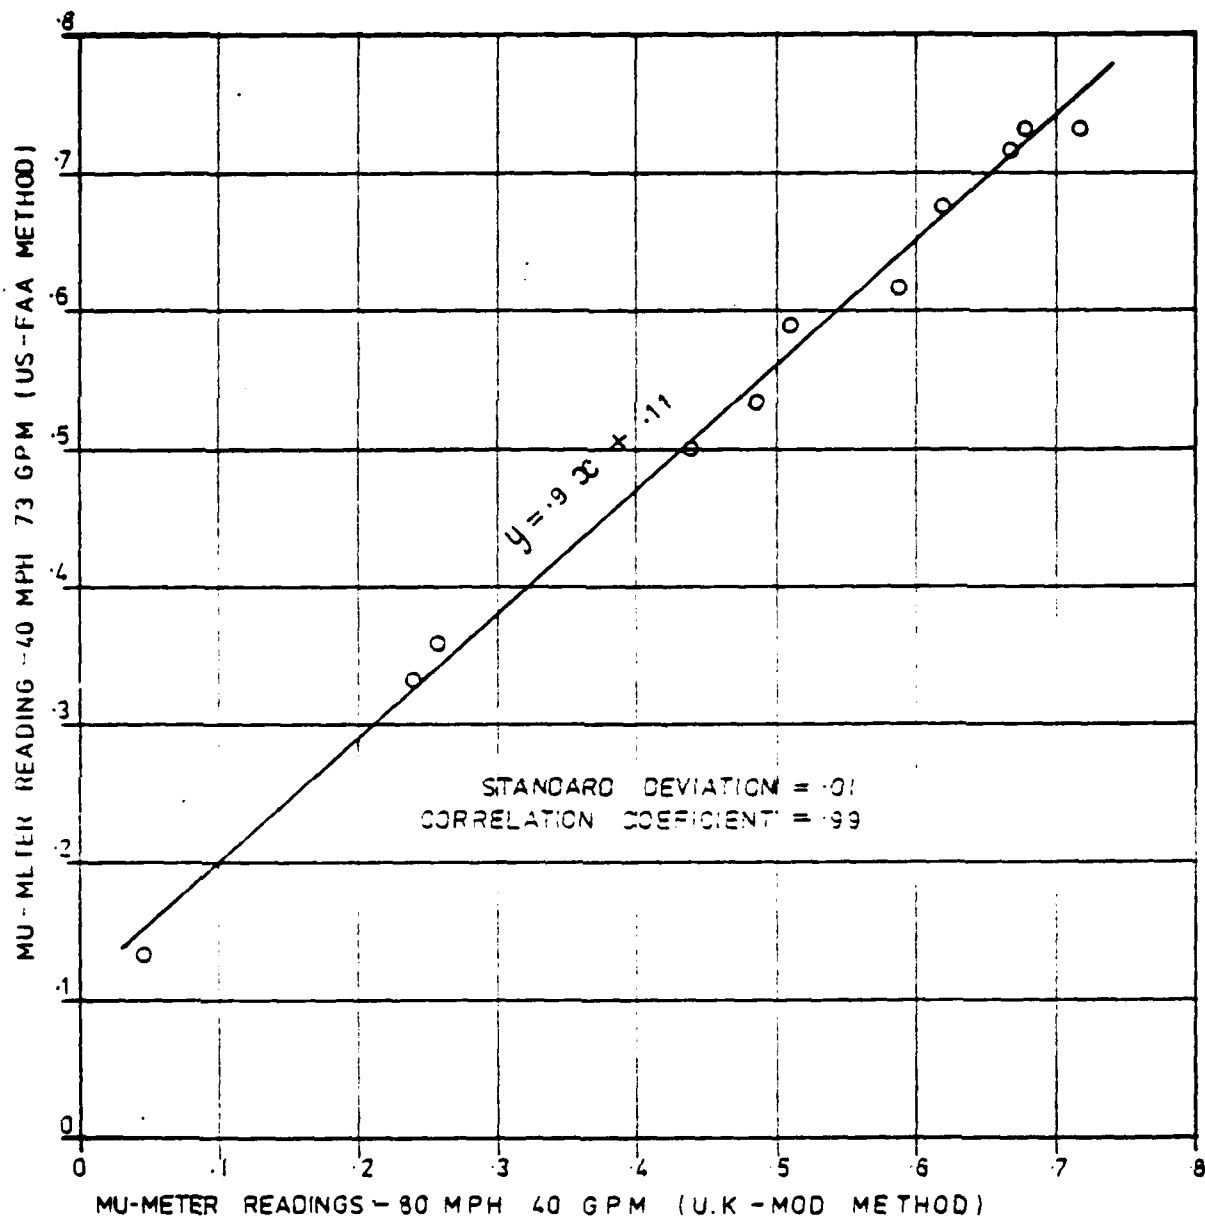

RELATIONSHIP BETWEEN MU-METER READINGS USING U.S. FEDERAL AVIATION ADMINISTRATION AND U.K. MINISTRY OF DEFENCE SELF WETTING METHODS.

FIG. 9


MU-METER RUNWAY FRICTION CLASSIFICATION TO DRAFT STANAG 3811 FS

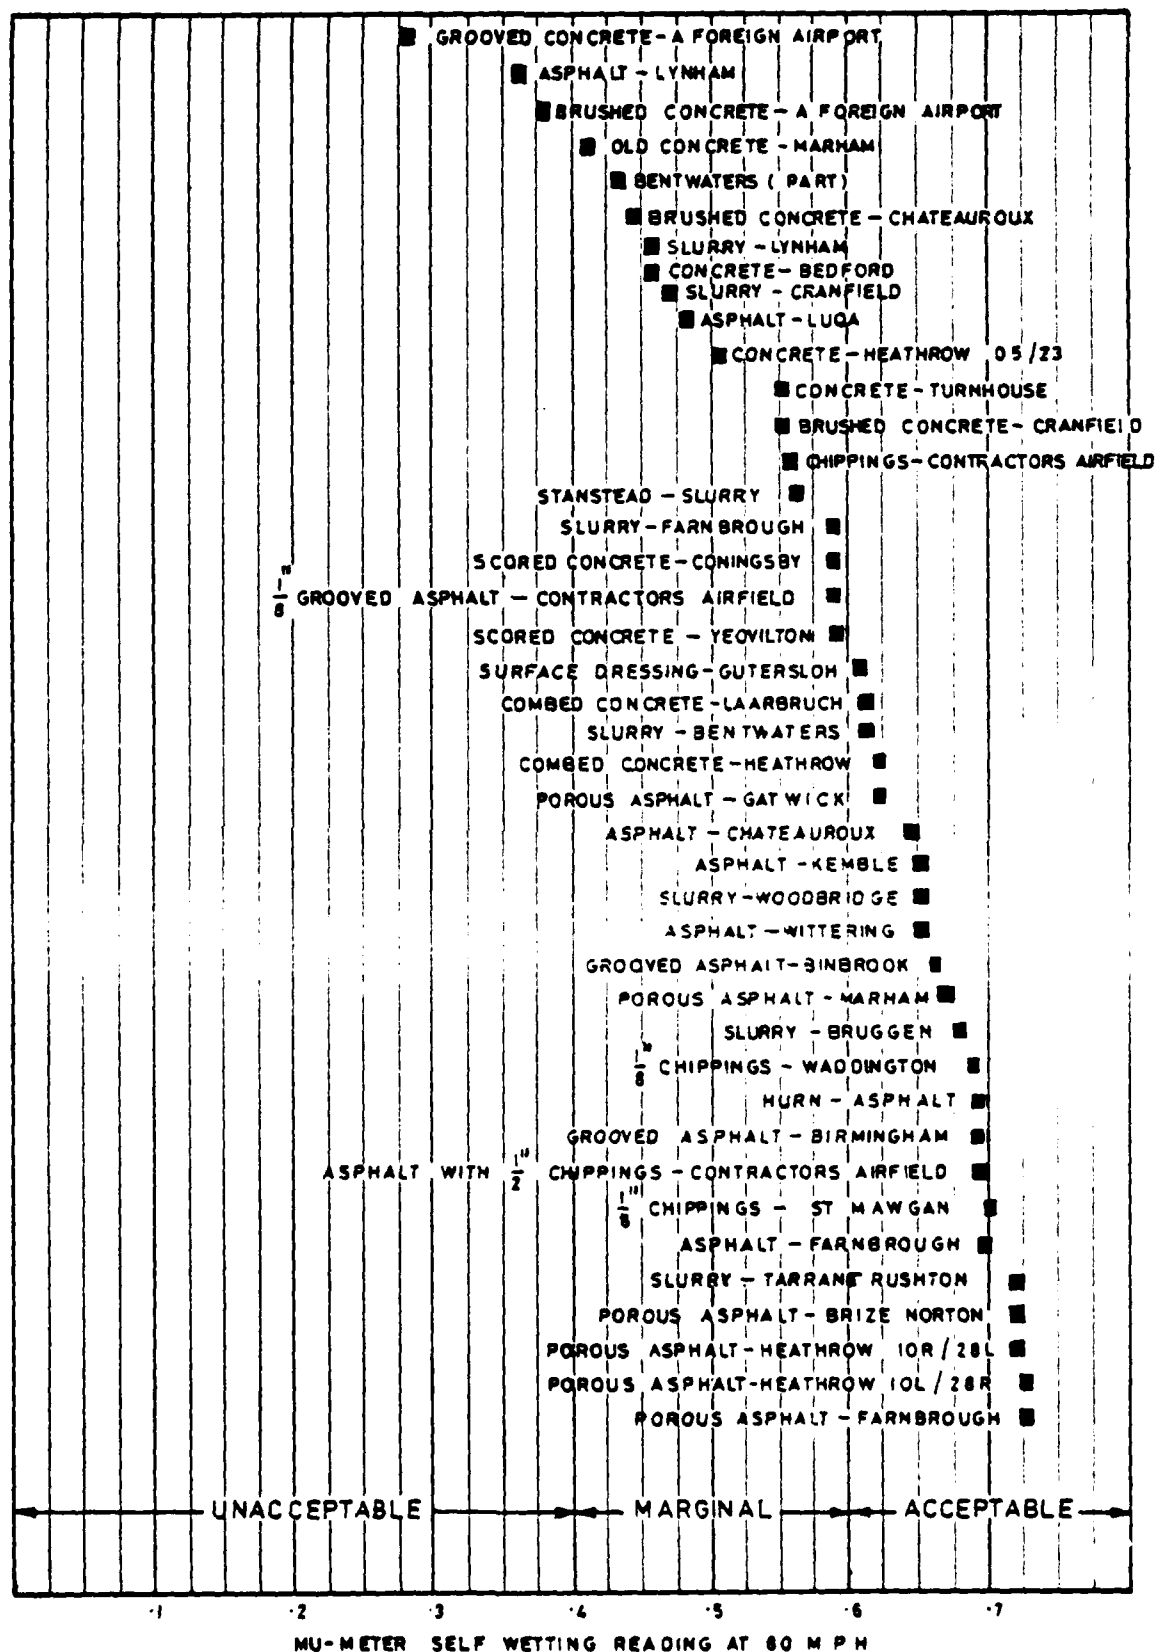

NOTE 1-SOME OF THESE RUNWAYS HAVE BEEN RESURFACED SINCE TESTING

NOTE 2-THE READINGS RECORDED ARE FOR THE MAIN PORTION OF THE RUNWAY

FIG.10

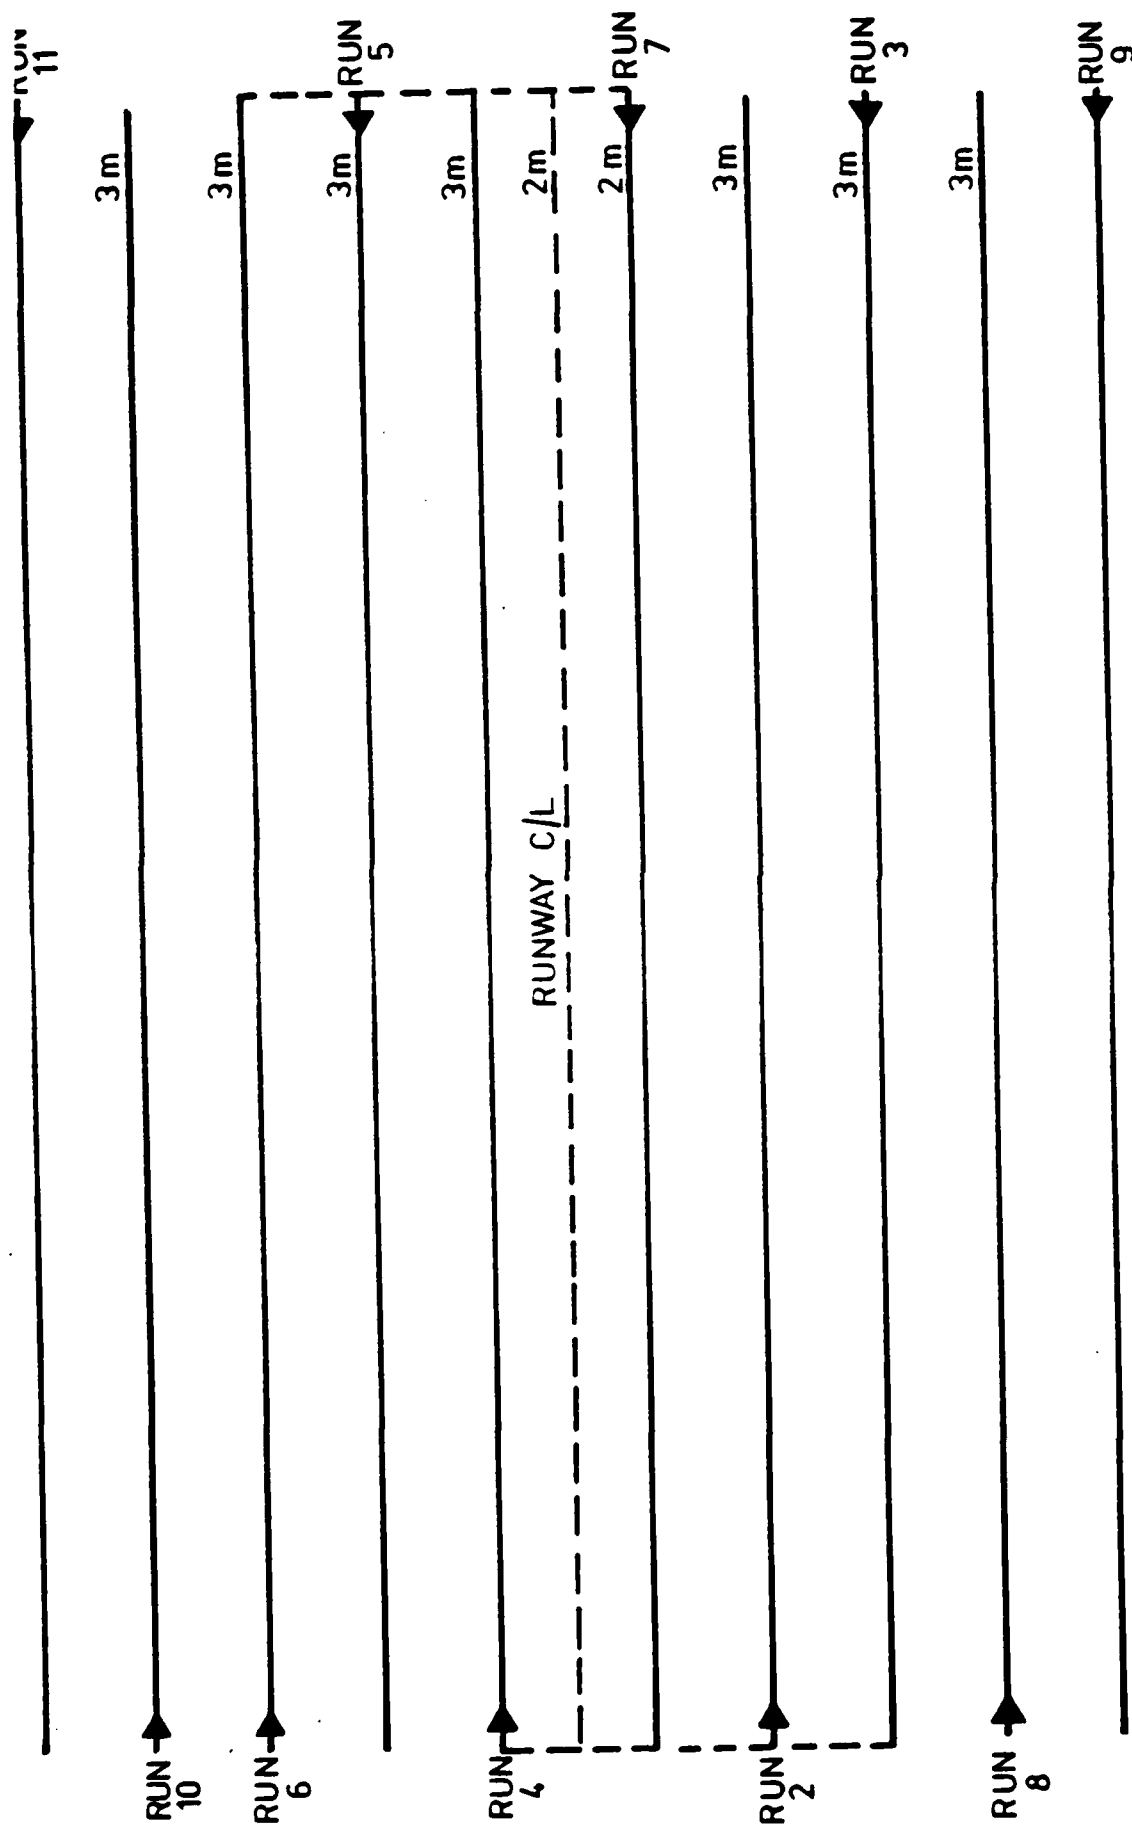

* RUN 1 IS RECHECKED AT RUN 7 TO ASSESS ANY CHANGES IN CONDITIONS. RUN 8 ONWARDS DEPENDS ON THE WIDTH OF RUNWAY BEING ASSESSED

FIG.11


RAF STATION.....
DATE
OPERATORS.....
.....

TOW VEHICLE	REGISTRATION	RAINFALL	COMMENT
			(eg Rainfall due prior to test)

(eg Rainfall during hour prior to test)

[illegible]

FIG. 12

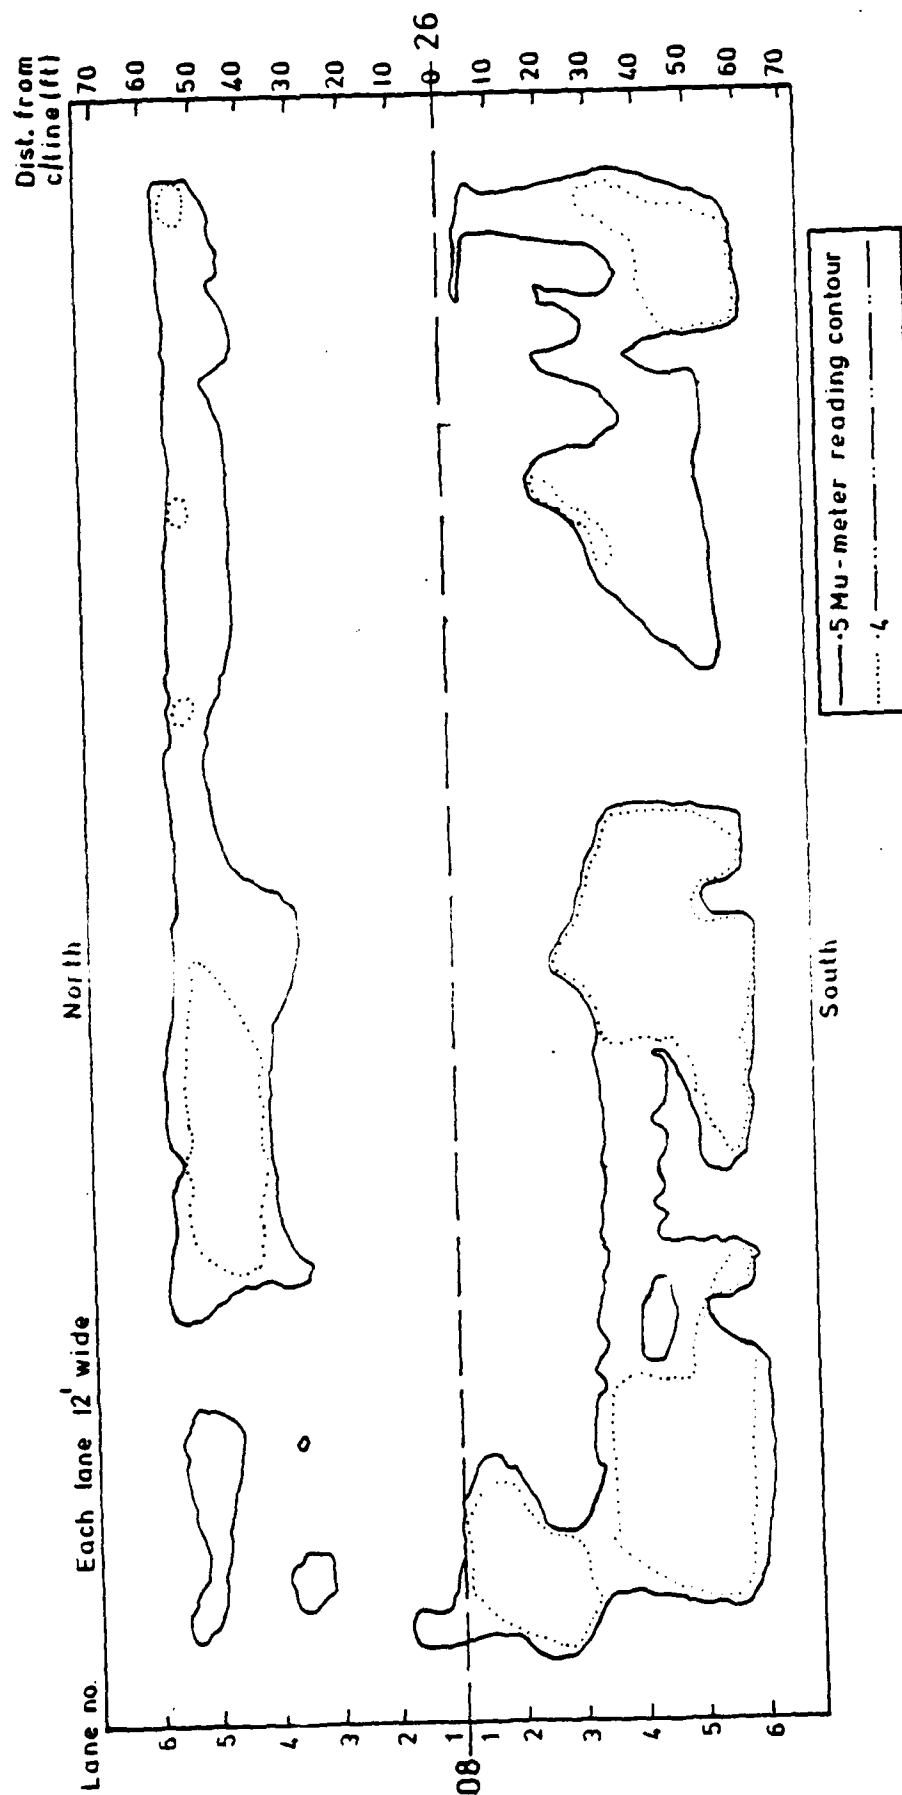

FRICTION CONTOURS ON A CIVIL RUNWAY

FIG.13

Runway Friction Classification

RAE West Freugh
Parts 1 & 2

by I Beaty
R J Nicholls

Cranfield Institute of Technology

Issue 2
November 1978

RAE WEST FREUGH

Part 1 - High Speed Tests.

INTRODUCTION

Part 1 of this note describes a runway friction classification carried out on 6th November 1978 at RAE West Freugh by Cranfield Institute of Technology.

RUNWAY DESCRIPTION

Fig.A1 is a schematic diagram of runway 07/25 which is 6023 ft. long and 150 ft.wide. The surface is of rolled asphalt with $\frac{1}{4}$ -inch chippings. The surface texture varies along the runway, depending on the proportion of these chippings which appear above the general asphalt surface (see Plate 3). Approximately 500 ft. at each threshold is concrete.

TEST EQUIPMENT

Mu-Meter MLE 374 towed by a Ford Capri incorporating a self-wetting device capable of depositing approximately .015 inches of water beneath the Mu-Meter measuring wheels was used for the tests (Plates 1 and 2).

RESULTS

The results are shown in Table A1, the attached proforma, and in the traces of the five runs made at 80 mph (Figs.A2-A6). Two runs (Nos.9 and 10) were made at 40 mph with the water flow adjusted to give the same depth as at 80 mph. Two short runs (Nos.7 and 8) of approximately 1000 ft. each were made at 20 mph and 60 mph, once again with standard water depth so that, together with an average of the 80 mph runs and an average of the 40 mph runs, a speed/friction curve could be plotted as shown in Figure A7. The resultant curve shows a Mu-Meter value which decreased only slightly with speed indicating that this surface has good friction properties over a wide range of speeds.

Rubber deposits at both ends are light.

DISCUSSION

The traces give an average friction reading at 80 mph of .72 which is classified as good. The reading along the runway edge (Fig.A6 run 6) at .70 shows that trafficking has raised the adjacent to centreline readings slightly.

CONCLUSIONS

1. With an average Mu-Meter reading of .72 with self-wetting at 80 mph, this runway is classified as good.

RAE WEST FREUGH

DETAILS OF MU-METER RUNS ON RUNWAY 07/25.

Run No	Direction	Speed mph	Self Wetting	Distance from G_L	μ_{07}	μ_c	μ_{25}
1	25	40	Off	5'S	.77	.77	.77
2	07	80	On	10'S	*	.67	.73
3	25	80	On	15'S	.72	.71	*
4	07	80	On	10'N	*	.75	.77
5	25	80	On	15'N	.71	.72	*
6	07	80	On	50'S	*	.70	.70
7	25	20	On	5'N	-	-	.77
8	25	60	On	5'N	.77	-	-
9	07	40	On	20'S	.74	.76	.77
10	25	40	On	20'N	.77	.79	.76
11	07	40	Off	5'S	.83	.825	.81
12	25	40	Off	5'S	.79	.79	.795

TABLE A 1

* No reading - vehicle accelerating.

μ_{07} Friction reading for 1/3rd of runway at 07 end.

μ_c Friction reading for 1/3rd of runway central.

μ_{25} Friction reading for 1/3rd of runway at 25 end.

RUNWAY CLASSIFICATION PROGRAMME PROFORMA

Report on test at RAE WEST FREUGH Aerodrome

SECTION 1

Date of test: 6-11-78

Time: 17.30

Weather: CLOUDY DAY

Wind: 20Kts

Direction: 180°

Runway direction: 07/25

Length: 6023'

Width: 150'

Runway surface description: ASPHALT

Runway surface condition (swept/unswept etc): SWEEP

Runway rubber deposits (location and approx extent) LIGHT

Confirm runway DRY before tests: ✓

SECTION 2

Tests conducted by: Cranfield Institute of Technology Towing vehicle: Ford Capri

Mu-Meter calibrated on test board before beginning test. Value was: .77

Confirm self-wetting device set at 40 galls per minute: ✓

Confirm test speed of 80 mph: ✓

SECTION 3 - Friction Measurements (Wet)

Note: Measurements to be made in both directions along tracks spaced 15 feet each side of centreline and in one direction along a track 20 feet from runway edge (middle third only).

15' South of centreline		
	Runway Hdg. <u>07</u>	Reciprocal Hdg. <u>25</u> ...
1st third	*	*
2nd third	<u>67</u>	<u>71</u>
3rd third	<u>73</u>	<u>72</u>
Trace	<u>2</u>	<u>3</u>

15' North of centreline		
	Runway Hdg. <u>07</u>	Reciprocal Hdg. <u>25</u> ...
1st third	*	*
2nd third	<u>75</u>	<u>72</u>
3rd third	<u>77</u>	<u>71</u>
Trace	<u>4</u>	<u>5</u>

20' from N/S edge	
	Runway Heading <u>07</u> ...
Middle third	<u>70</u>

Length covered by traces.

Trace No. 2... Starting at 2143.ft from t/hold r/wy. 07... and ending 640.ft from t/hold. 25...

Trace No. 3... Starting at 2179.ft from t/hold r/wy. 25... and ending 640.ft from t/hold. 07...

Trace No. 4... Starting at 2267.ft from t/hold r/wy. 07... and ending 589.ft from t/hold. 25...

Trace No. 5... Starting at 2338.ft from t/hold r/wy. 25... and ending 764.ft from t/hold. 07...

The original traces, annotated to give reasons for any significant variations in Mu-Meter values, must be attached to this form.

SECTION 4 Remarks

* Vehicle accelerating - No reading

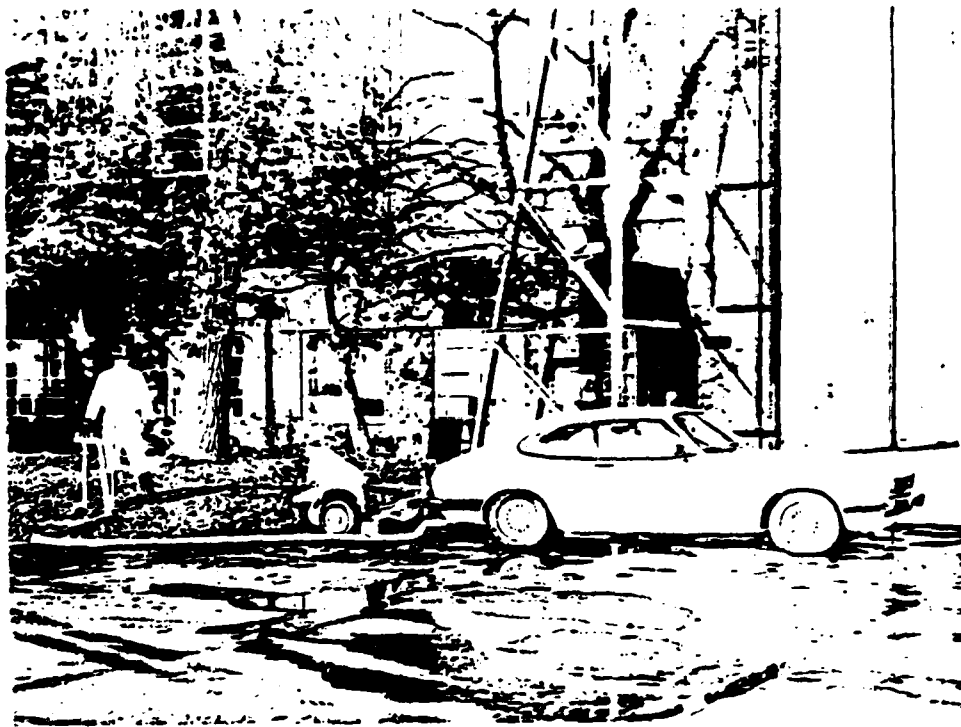


Plate 1 Mu-meter and tow vehicle

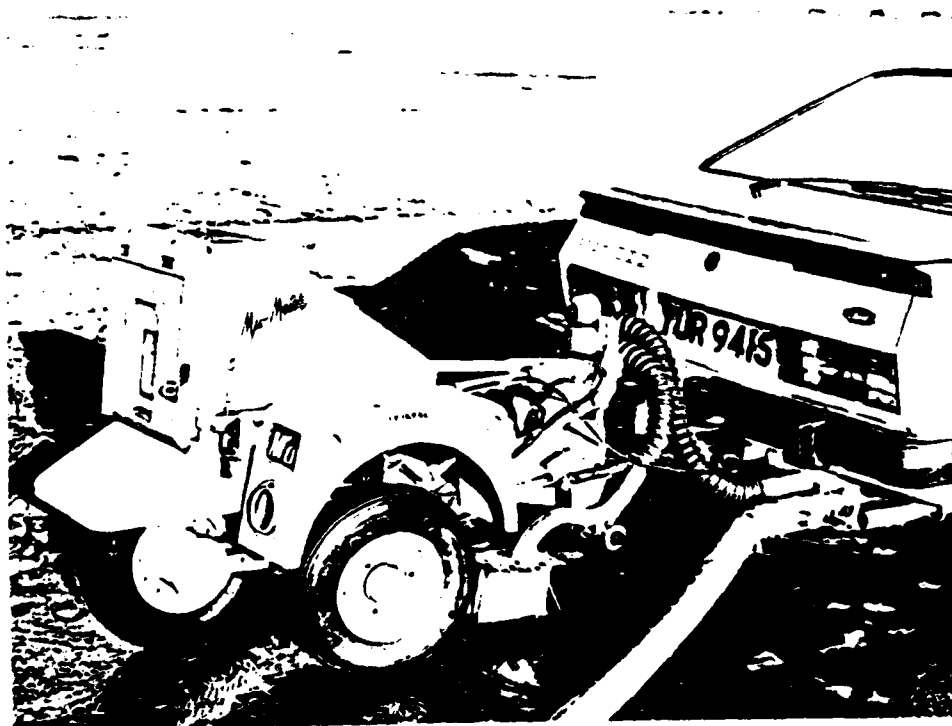


Plate 2 Self-wetting system

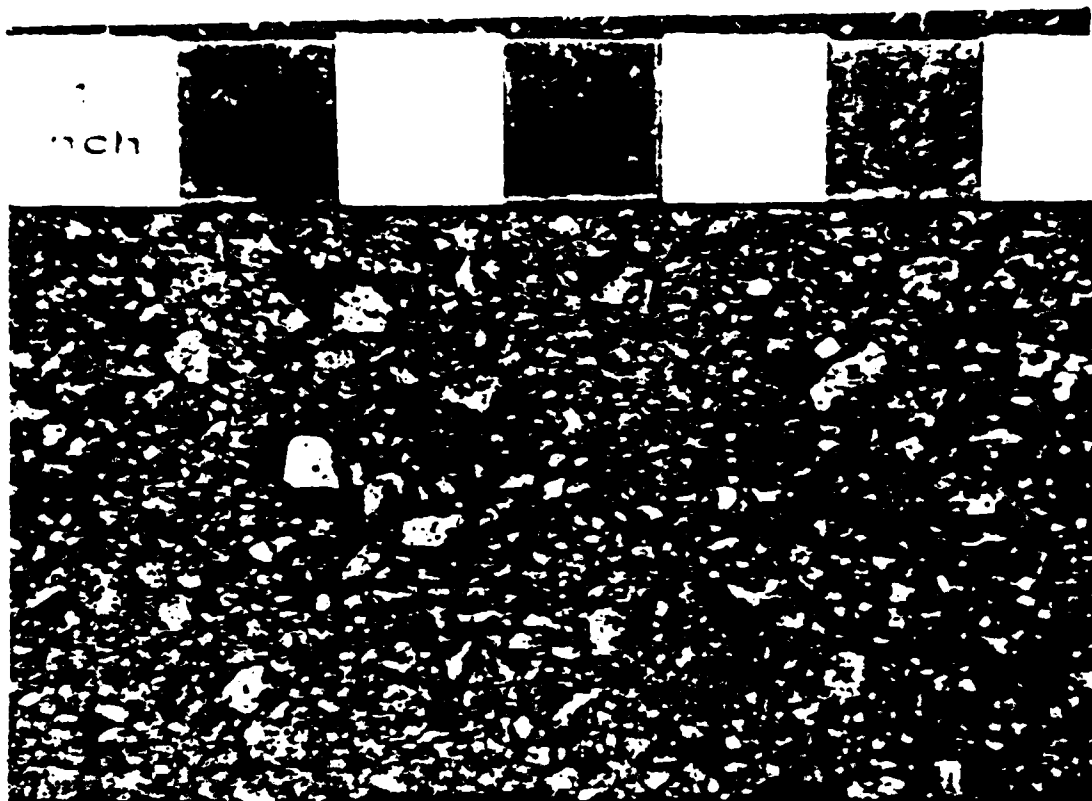


Plate 3 Asphalt

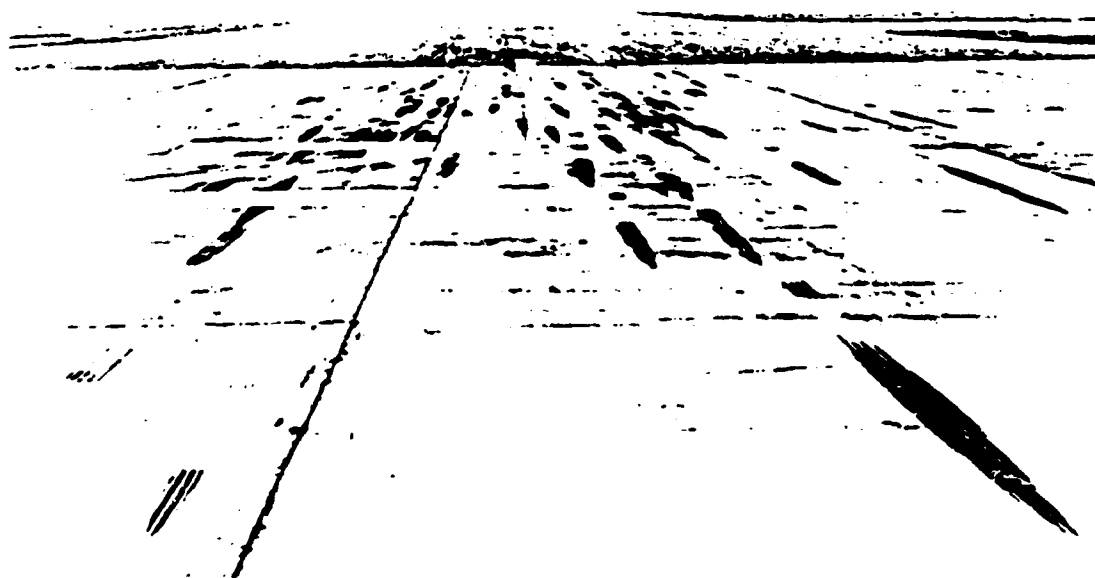


Plate 4 Rubber deposits 25 threshold

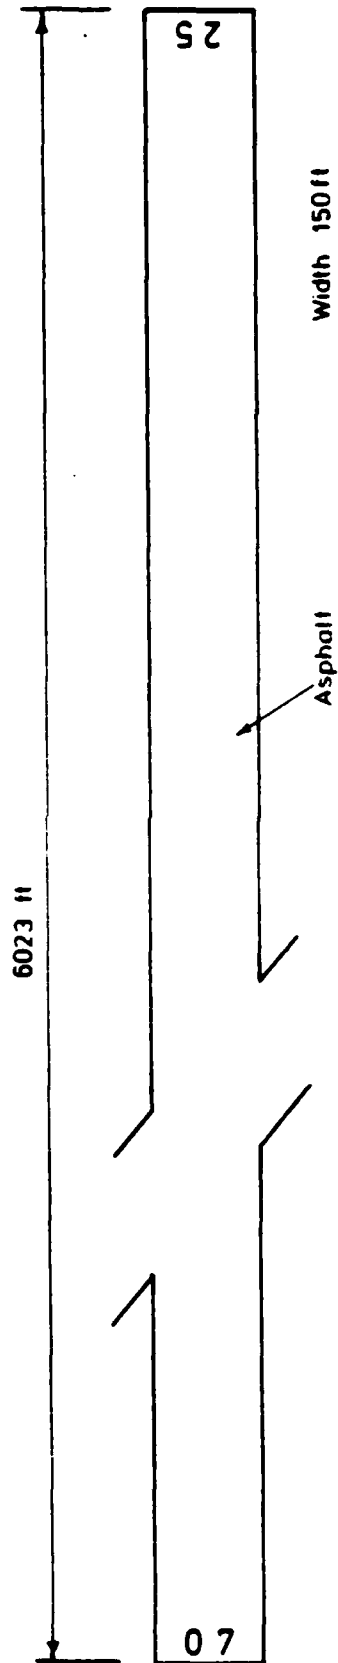


Fig A1 RAE West Freugh. Schematic diagram of runway 07/25

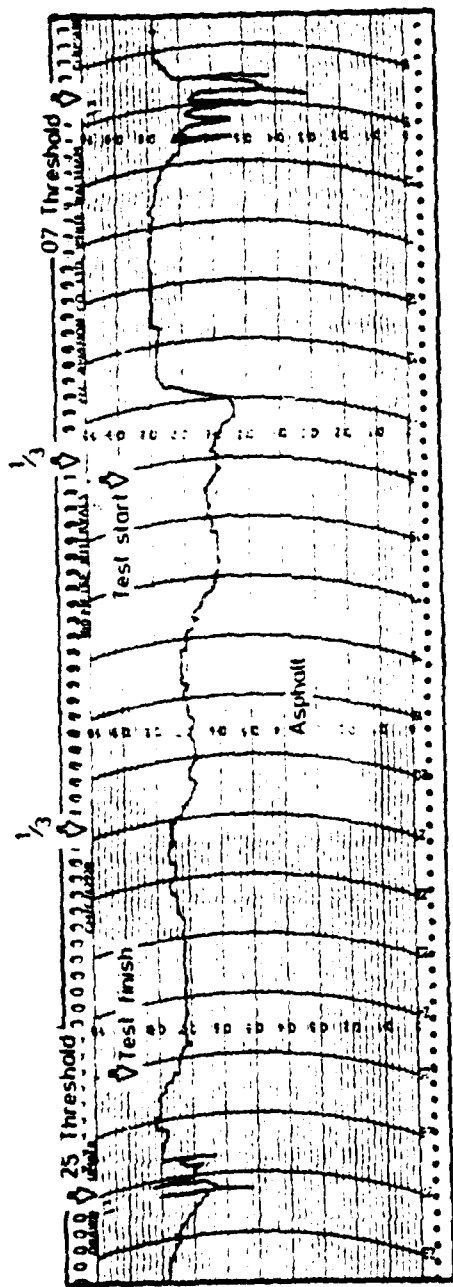


Fig A2 Runway 07 10'S of centreline

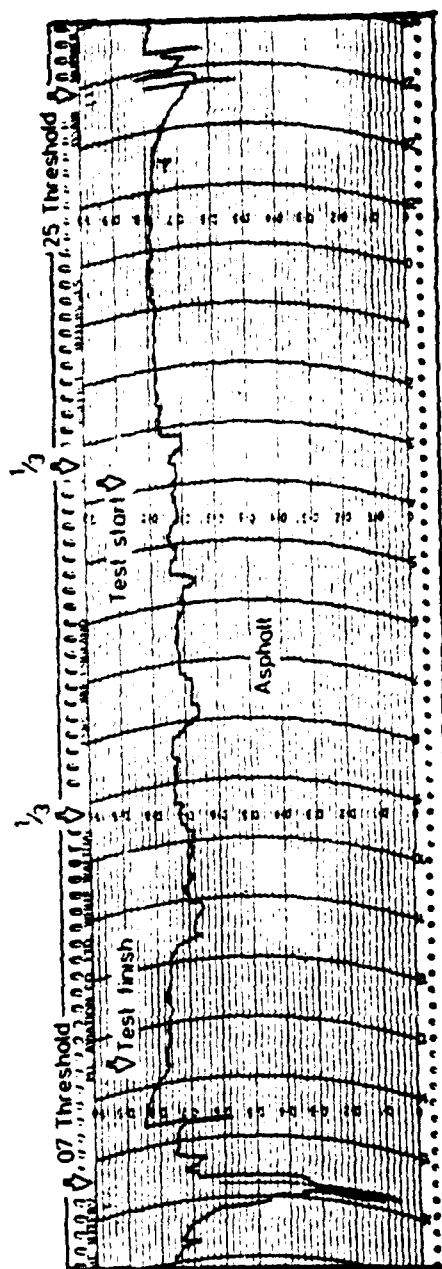


Fig A3 Runway 25 15'S of centreline

Scale 1 2

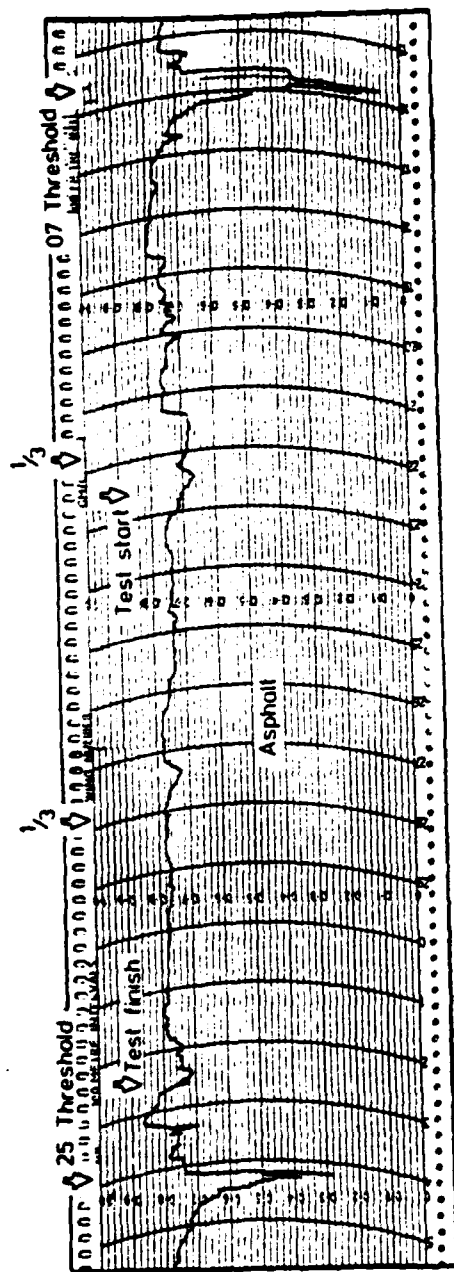


Fig A4 Run 4 Runway 07 10N of centreline

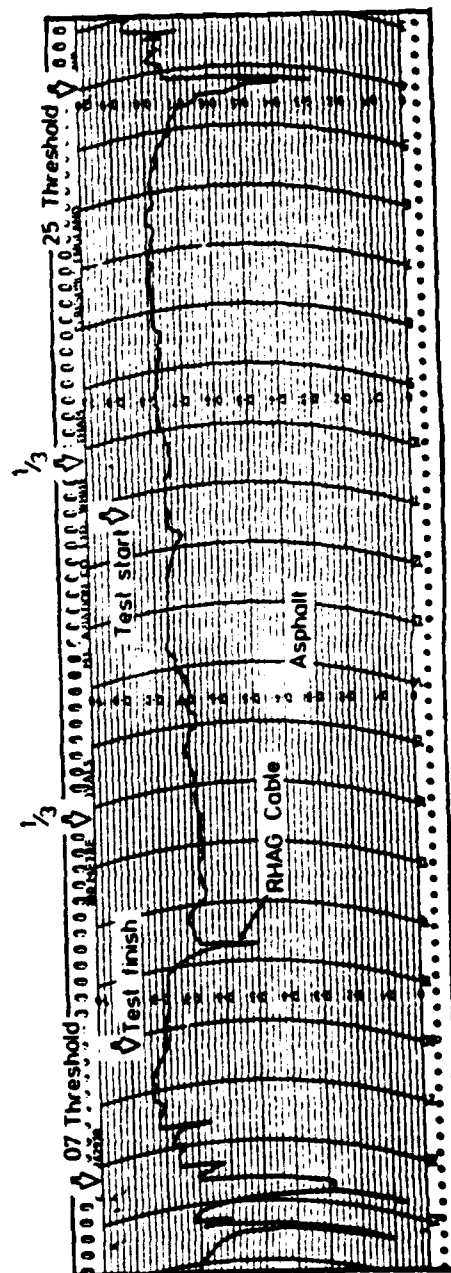


Fig A5 Run 5 Runway 25 15N of centreline

Scale 1:2

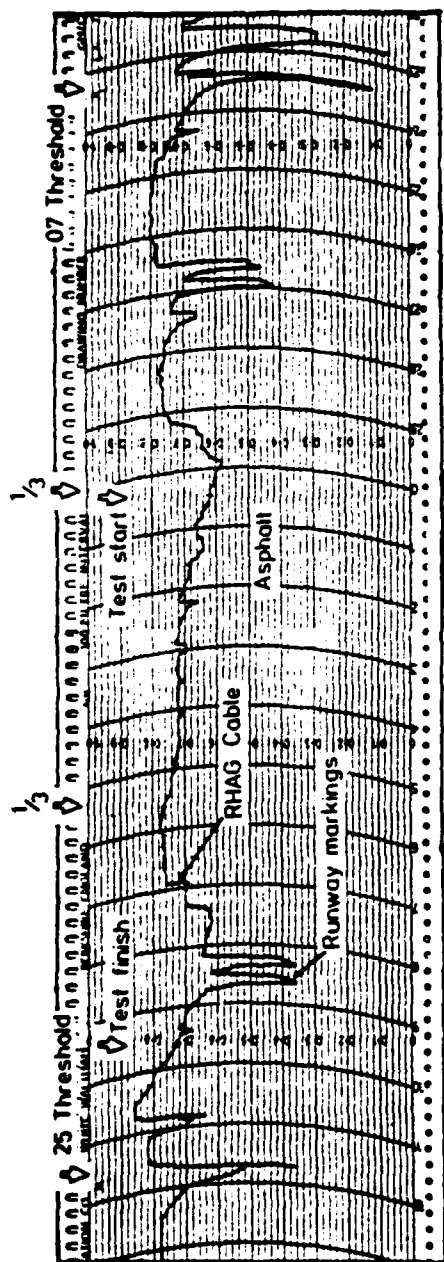


Fig A6 Run 6 Runway 07 50'S of centreline

Scale 1:2

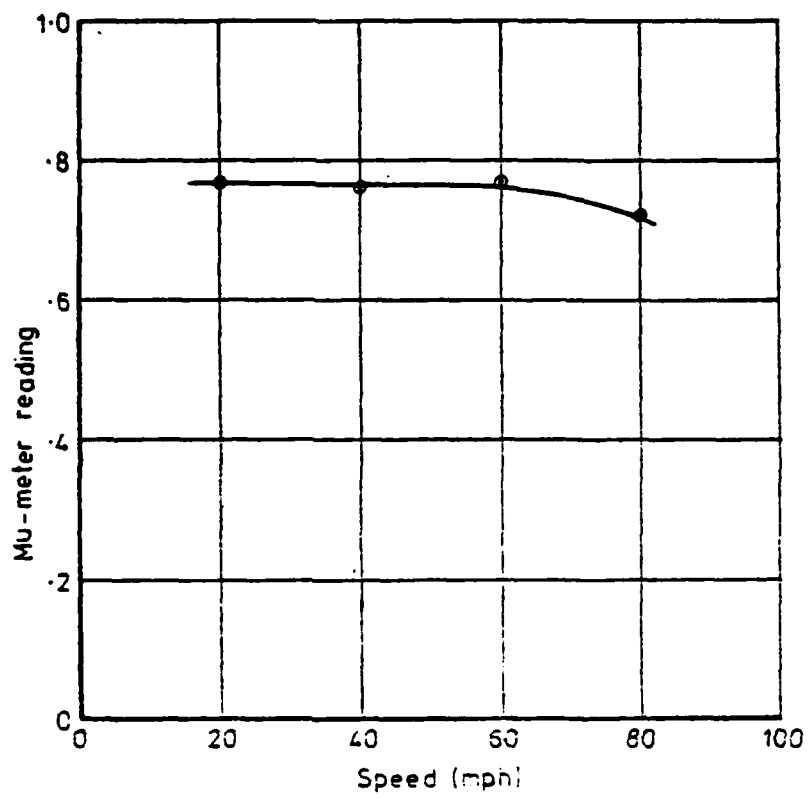


Fig A7 Mu-meter reading v Speed

RAE WEST FREUGH

Part 2 - Low Speed Tests

INTRODUCTION

Part 1 of this classification report dealt with the friction qualities of the West Freugh 07/25 runway under controlled wetting conditions (constant water depth) at a Mu-Meter speed of 80 mph. Part 2 considers the friction qualities under natural rainfall conditions which, unlike Part 1, will identify any areas of low friction caused by standing water or ponding. Part 1 measured the friction within 15 ft. (4.5m) of the centreline and along one edge, whilst Part 2 covers measurements over the central 60 ft. (18m) of the runway.

These trials were conducted by airfield personnel in accordance with NATS document 8K/182/115. The Mu-Meter traces were subsequently analysed by CIT Cranfield.

RESULTS

It must be noted that no record of actual rainfall amounts was made. Consequently, whilst these results show what occurred at the time of the trial, they may only be used as a guide to potential low friction areas.

Table A2 gives a breakdown of the results averaged over every third of the runway. It can be seen that in general the further from the centreline, the lower the Mu-Meter reading. Fig. A8 is a copy of a typical Mu-Meter trace (Run 3, 26 ft. (8m) from the centreline).

Fig. A9 shows a friction contour map of the 07/25 runway obtained by isolating from the Mu-Meter traces the low friction areas (below .5 and .4 Mu-Meter reading) detected during each run. These areas have been transferred on to a scaled diagram of the runway and then linked by contour lines to show potential low friction areas.

Two major low friction areas are identified.

1. North of centreline extending from 600 ft. to 2000 ft. from the 07 threshold and 30 ft. wide.
2. South of centreline extending from 3200 ft. to 5500 ft. from the 07 threshold 30 ft. wide.

Other smaller areas of low friction can also be seen.


The low friction must be caused by depth of water since Phase 1 has shown that, under constant water depth, the Mu-Meter value is reasonably constant.

Run No.	Direction	Distance from Centreline	Mu-Meter Reading		
			μ_{07}	μ_c	μ_{25}
1	07	2m S	.73	.75	.67
2	25	5m S	.66	.64	.51
3	07	8m S	.56	.60	.48
4	25	2m N	.59	.61	.68
5	07	5m N	.62	.64	.60
6	25	8m N	.57	.56	.51

Table A2 Details of 40 mph Mu-Meter runs during moderate continuous rainfall.

CONCLUSIONS

1. Part 1 has shown that under controlled wetting conditions, the Mu-Meter readings on runway 07/25 at West Freugh are good.
2. Part 2 identifies a number of areas of low Mu-Meter readings which are probably due to areas of standing water or ponding.

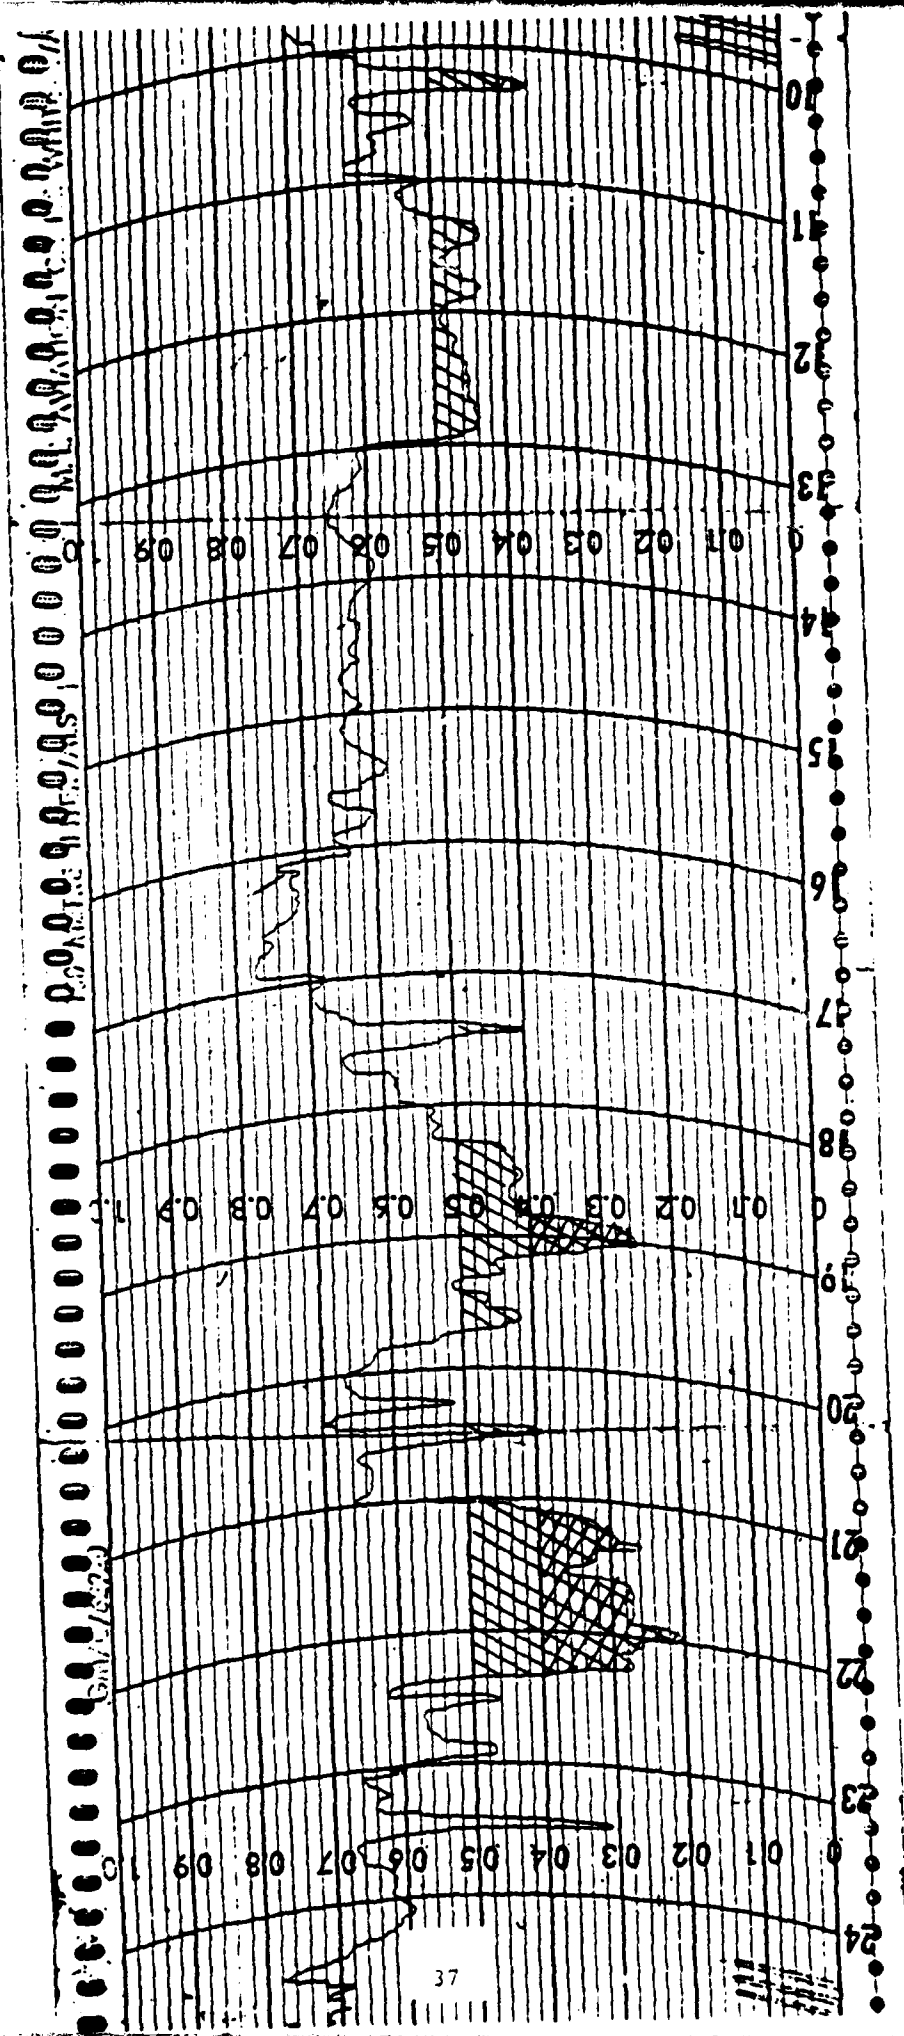

FigA8 Typical Mu-meter trace during rainfall showing
low friction areas caused by ponding

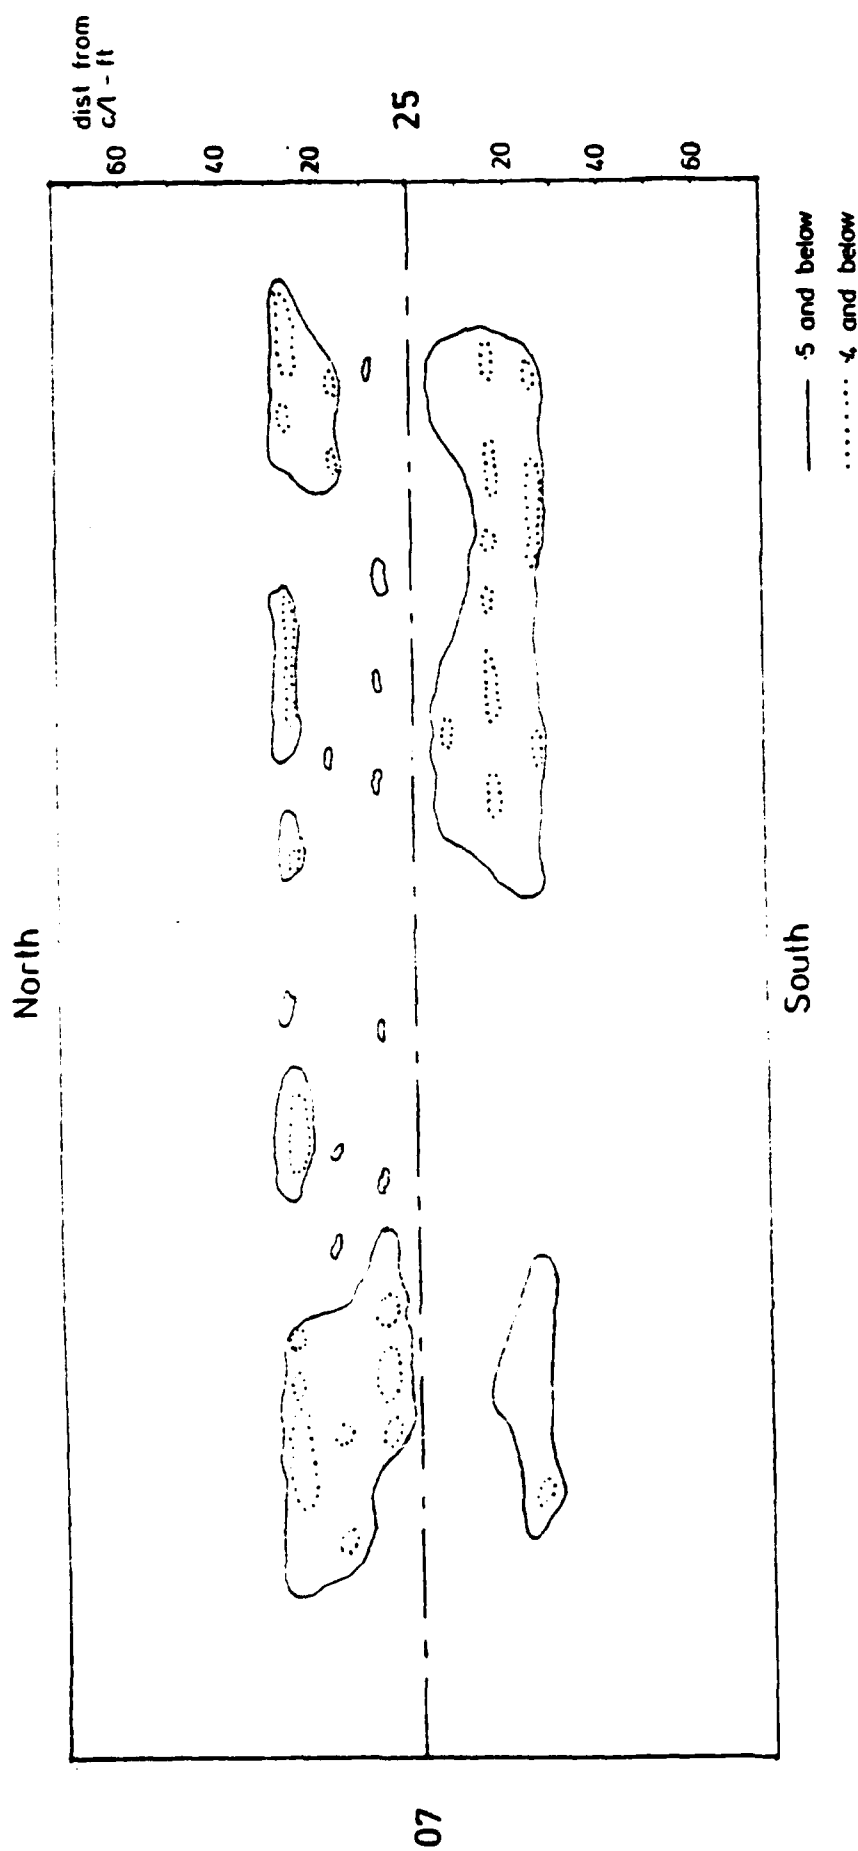


Fig A 9 Friction contour map of RAE West Freugh runway

REPORT DOCUMENTATION PAGE

(Notes on completion overleaf)

Overall security classification of sheet **UNLIMITED**

(As far as possible this sheet should contain only unclassified information. If it is necessary to enter classified information, the box concerned must be marked to indicate the classification eg (R), (C) or (S)).

1. DRIC Reference (if known)	2. Originator's Reference	3. Agency Reference S&T-MEMO-6-79	4. Report Security Classification UNLIMITED
5. Originator's Code (if known) 7210000X	6. Originator (Corporate Author) Name and Location Procurement Exec., Min. of Defence, DA Mech., UK		
5a. Sponsoring Agency's Code (if known) 7273000C	6a. Sponsoring Agency (Contract Authority) Name and Location Procurement Exec., Min. of Defence, UK		
7. Title THE FRICTION CLASSIFICATION OF RUNWAYS			
7a. Title in Foreign Language (in the case of translations)			
7b. Presented at (for conference papers). Title, place and date of conference			
8. Author 1. Surname, initials SUGG, R.W.	9a. Author 2 BEATY, I.	9b. Authors 3, 4... NICHOLLS, R.J.	10. Date pp ref 12.1979 42 4
11. Contract Number	12. Period	13. Project	14. Other References
15. Distribution statement			
Descriptors (or keywords) *Aircraft landing, *Aquaplaning, *Friction, *Runways, *Surface waters, Measuring instruments, Standards, Surface properties, Wettability.			
Abstract The fundamental principles regarding the design of runway surfaces to provide high friction under wet conditions are well known and have been put into practice for some time. In the past a locked wheel trailer has been used to assess the relative friction of runways by making measurements at a number of isolated points on the surface. With the development of the Continuous Recording Runway Friction Meter (Mu-Meter) and a runway self wetting system contained in the tow vehicle, it has been possible to obtain a permanent record showing the friction reading along the entire length of a runway. This S&T Memo describes the method developed to carry out such a trial together with its associated Standard Friction Classification Table. Use of the Mu-Meter under natural rain conditions has demonstrated that aircraft aquaplaning			

NOTES ON COMPLETION OF REPORT DOCUMENTATION PAGE

This Documentation Page is designed specifically for MOD reports and reports produced by Contractors.

Boxes marked* below need be completed only if the information is readily available.

- *1. DRIC reference: Enter DRIC reference (BR number) if one has been assigned.
2. Originator's Reference: Enter the report number by which the document is identified by the originator of the report, in the form in which it appears on the cover.
3. Agency reference: Enter reference number allocated by sponsoring agency (contract authority) in the case of contract reports.
4. Report Security Classification: Enter security classification or marking which limits the circulation of the report, or enter UNLIMITED when this applies.
- *5. Originator's Code: Code number for the DRIC-standardised form of the entry appearing in Box 6.
- *5a. Sponsoring Agency's Code: Code number for the DRIC-standardised form of the entry appearing in Box 6a.
6. Originator (corporate author): Enter name and location of the organisation preparing the report.
- 6a. Sponsoring Agency (Contract Authority): Enter the name of the monitoring MOD Branch or Establishment in the case of Contractor's reports. If an MOD report covers work funded by an outside agency, enter the name of that agency.
7. Title: Enter the complete report title in capital letters but omitting initial definite or indefinite articles. If the report covers a specific period, enter this after the title, eg (1.1.1972-31.3.1972).
- 7a. Title in Foreign Language: In the case of translations, enter the foreign language title (transliterated if necessary) and the translated English title in Box 7.
- 7b. Conference Papers: If 7 is the title of a paper presented at a Conference, or a Conference proceedings, enter the Conference Title, where it was held and the date.
8. Author 1: Enter the name of the first author, followed by his initials.
- 9a. Author 2: Enter the name of the second author, followed by his initials.
- 9b. Authors 3,4,...: Enter third and following authors' names.
10. Date: Enter the month (in figures) and the year of the report (Dec., 1969 is written 12.1969). If the report is undated but a period covered by the report is indicated, enter the date at the end of the period, pp.ref. Enter the inclusive number of pages in the report containing information, i.e. including appendices, tables and illustrations, and the total number of references cited.
11. Contract Number: Enter the number of the contract or grant under which the report was written.
12. Period: (always associated with the Contract Number). Only to be used for reports covering a specific period, e.g. quarterly, annual or final reports. Enter OR-1, AR, FR, as appropriate.
13. Project: Enter project name or number.
14. Other Reference: Enter any reference, other than those in Boxes 1 or 2, by which the report may be identified.
15. Distribution statement. Enter any limitations on the distribution of the document. If distribution is limited to particular groups eg MOD, MOD and its Contractors, etc. it should be stated. If the distribution is the responsibility of another authority eg a HQ Directorate (Technical Policy Authority) enter "Distribution controlled by MOD Technical Policy Authority". Enter "via DRIC" after "Authority" where appropriate and name the Technical Policy Authority if possible.

Descriptors: Any number of descriptors (or key-words) can be entered. If selected from a published thesaurus, eg The Thesaurus of Engineering and Scientific Terms (TEST), this should be indicated.

Abstract: The abstract should preferably not exceed 150 words, i.e. it can be considerably shorter than the Abstract to be provided on the Title Page of the Report. Information available in the report title need not be included in the abstract.

could sometimes occur in local areas. A method is described how these areas can be identified and how it is combined with the self wetting trial to give a proper friction evaluation of a runway.

The relationship in Mu-Meter readings when using the US Federal Aviation Administration and UK Ministry of Defence methods of runway friction classification, have been determined.